

## PAPER

[View Article Online](#)  
[View Journal](#) | [View Issue](#)

Cite this: *Polym. Chem.*, 2025, **16**, 538

# Synthesis and cell-induced luminescence of post-functionalisable ionisable polyesters from the Passerini 3-component polymerisation†

Lewis O'Shaughnessy,<sup>a</sup> Akosua Anane-Adjei,<sup>b</sup> Mariarosa Mazza,<sup>b</sup> Naoto Hori,<sup>a</sup> Pratik Gurnani<sup>c</sup>\* and Cameron Alexander<sup>a</sup>\*

Recent developments in polymer synthesis methods allow the preparation of new materials across a wide chemical space and with high atom efficiency. In this work, we developed a strategic approach to the synthesis of a diverse array of novel ionisable polyesters via a modular and iterative synthetic approach. We initially designed a range of diacid monomers and subsequently used the Passerini 3-component reaction as a simple, one-pot step growth polymerisation to build a library of novel, highly functionalised polymers. This library was expanded further by the application of thiol/ene and copper-initiated azide/alkyne click chemistries to introduce further structural diversity into the materials. Selected polymers were found to internalise readily in a model cell line (HEK-293T), and for a subset of these polymers, bright luminescence was observed in the cells upon internalisation, even though neither the cells, nor the polymers, were luminescent on their own at these wavelengths. Our synthetic approach offers a versatile platform for the systematic development and modification of novel macromolecules and for cell-labelling components.

Received 17th October 2024,  
Accepted 12th December 2024

DOI: 10.1039/d4py01165a

[rsc.li/polymers](https://rsc.li/polymers)

## Introduction

Multicomponent reactions (MCRs), which combine 3 or more components in a single, one-pot reaction, have revolutionised our ability to access complex products at high atom economy, high yield and in mild solvents whilst also providing orthogonality with multiple functional groups.<sup>1–3</sup> There now exists a wide range of MCRs, each of which combines a unique combination of substrates into a different product. For example, the Passerini 3-component reaction (P3CR) combines an aldehyde with a carboxylic acid and an isocyanide to form an  $\alpha$ -acyloxy amide.<sup>4</sup> Meanwhile, the A<sup>3</sup> reaction involves the reaction of aldehyde, an alkyne and an amine to form a propargyl-amine,<sup>5</sup> while further possibilities are offered by the Mannich reaction, which reacts a non-enolizable aldehyde with a primary or secondary amine and an enolizable carbonyl group to form  $\beta$ -amino-carbonyl compounds.<sup>6</sup> The enormous diversity in pro-

ducts derived from MCRs has enabled the development of high throughput combinatorial libraries to screen for putative drug products<sup>7</sup> and for the total synthesis of natural products.<sup>8</sup>

MCRs also represent an ideal strategy to impart complex chemical functionality to synthetic macromolecules, with the potential to encode previously inaccessible chemistries. There is now a growing body of literature reporting the use of MCRs in polymer chemistry. This includes P3CR chemistries to synthesise novel, multifunctional acrylate<sup>9</sup> or diene<sup>10</sup> monomers that can be subsequently polymerised to form networks and cross-linked materials. Subsequent work has also seen the P3CR utilised as a technique to functionalise polymers, with pendant carboxylic acid groups.<sup>11</sup> The Ugi 4-component reaction has similarly been used to generate diene monomers that were later polymerised by both acyclic diene metathesis and by thiol-ene addition.<sup>12</sup> The reaction has been used more broadly in polymer science as a method to link different components into block copolymers.<sup>13</sup> MCRs have also played a role in polymer post-modification, including the use of the Kabachnik-Fields reaction to generate  $\alpha$ -amino phosphonate motifs on polymer side chains,<sup>14</sup> whilst the Debus-Radziszewski reaction has been used to crosslink polymers by converting pendant amine groups into imidazolium groups.<sup>15</sup>

More recently, MCRs have been directly employed to produce polymers in multicomponent polymerisations (MCPs)

<sup>a</sup>Division of Molecular Therapeutics and Formulation, Boots Science Building, School of Pharmacy, University of Nottingham, Nottingham, NG7 2RD, UK.

E-mail: [cameron.alexander@nottingham.ac.uk](mailto:cameron.alexander@nottingham.ac.uk)

<sup>b</sup>Advanced Drug Delivery, Pharmaceutical Sciences, R&D, AstraZeneca, UK

<sup>c</sup>UCL School of Pharmacy, University College London, 29-39 Brunswick Square, Bloomsbury, London, WC1N 1AX, UK. E-mail: [p.gurnani@ucl.ac.uk](mailto:p.gurnani@ucl.ac.uk)

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d4py01165a>



where several units are incorporated as single monomers in the repeating polymer chain. Most commonly this has been exploited using an AB + C type step growth MCP including the P3CR,<sup>16–18</sup> Ugi 4-component reaction<sup>19</sup> and the Debus–Radziszewski reaction,<sup>20</sup> but has also been conducted *via* an A2 + B2 route.<sup>10</sup> One of the key advantages of MCPs is the ability to produce a chemically diverse library of synthetic macromolecules often imparting more than one pendant functional group per repeating unit in a single polymerisation step.

Of these MCP techniques, the Passerini-3 component polymerisation (P3CP) remains among the most popular due to its mild conditions with high yields, 100% atom economy, minimal by-products and use of simple acids, aldehydes and isocyanides.<sup>17,21–25</sup> P3CP is a relatively recent development, first reported in 2011 *via* so-called A2 B2 monomers, when simple, unfunctionalized diacid and dialdehyde monomers were combined with four different isocyanides.<sup>10</sup> AB type P3CP was later established in 2014, when novel aldehyde/acid monomers were prepared, which were then successfully reacted with a range of isocyanides.<sup>16</sup> Subsequently, more functionalised monomers have been successfully integrated into the reaction, resulting in polymers that display a large variety of addressable chemistries.<sup>18,22,24,26</sup> Recent advances have seen a number of novel macromaterials synthesised *via* the P3CR and P3CP, including light<sup>27</sup> and heat<sup>28</sup> responsive polymers, self-healing materials<sup>29</sup> and modified nanocellulose materials for peptide delivery.<sup>30</sup>

Accordingly, P3CP derived materials offer considerable promise for the development of novel biomaterials, as the diversity in functionality in many ways mimics those of natural polymers. Many current biomaterials are derived from proteins and polysaccharides because of this high functionality, and also due to their intrinsic biodegradability and established biological properties.<sup>31</sup> The most explored applications are in wound healing, implants, tissue regeneration scaffolds and drug delivery.<sup>32</sup> Synthetic polymers have the potential to replace some of these natural macromolecules in biomaterials applications, as the additional chemical versatility they offer allows the tailoring of properties specifically towards the desired application.<sup>31</sup> Passerini derived polymers have a great advantage as biomaterials because they are derived from ester and amide linkages, so are likely to be biodegradable.<sup>17,22,26,33</sup> In addition, the range of functional groups tolerated by the reaction allows for the synthesis of materials that can be used as prepared or modified further according to the intended use.

Polycationic biomaterials have been used to enhance drug delivery into cells and as carriers for nucleic acid therapeutics and vaccines.<sup>34–39</sup> In addition, a number of polycationic materials have shown intrinsic antibacterial and antifungal properties, owing to their ability to bind to or disrupt cellular membranes.<sup>40,41</sup> Accordingly, there is considerable interest in expanding the toolkit for synthesising ionisable polymers and in making libraries of these materials for biological screening.<sup>33,37–39</sup> However, the original P3CP reaction is incompatible with primary amine groups, as this leads to

competition with the Ugi 4-component reaction, instead forming a bis-amide.<sup>42,43</sup> Therefore, although ionisable RAFT polymers have been synthesised from P3CR-derived monomers,<sup>44</sup> the preparation of ionisable polymers by direct MCPs remains relatively unexplored. For this polymerisation approach to be translated towards materials or biological applications, there is a need for the development of new monomer families. In this work, we have generated a set of modular diacid monomers and exploited the A2 B2 approach to P3CP to develop a library of novel ionisable polymers. To the best of our knowledge, this is the first reported use of P3CP to directly synthesise protonatable polymers. The range of monomers studied allowed for the integration of a wide range of functionality into our materials, which could then be further enhanced by polymer post-modification *via* click-chemistries.

## Experimental

### Materials

The following chemicals were used as received: allylamine (Aldrich), propargylamine (Acros Organics), 1-(3-aminopropyl) imidazole (Aldrich), piperazine (Aldrich), *N,N*-dimethylethylenediamine (Aldrich), *N,N'*-dimethylethylenediamine (Aldrich), *N,N,N'*-trimethyldiethylenetriamine (ABCR), *tert*-butyl acrylate (Acros Organics), magnesium sulphate (Aldrich), acetyl chloride (Aldrich), *tert*-butyl isocyanide (Aldrich), cyclohexyl isocyanide (Aldrich), *n*-butyl isocyanide (Aldrich), methyl isocyanoacetate (Alfa Aesar), azobisisobutyronitrile (Aldrich), benzyl mercaptan (Aldrich), thioglycerol (Aldrich), 6-mercaptohexanol (Aldrich), 2-(dimethylamino)ethanethiol hydrochloride (Aldrich), pyridine (Aldrich), 3-mercaptopropionic acid (Aldrich), benzyl bromide (Aldrich), sodium azide (Aldrich), 3-bromo-propanol (Aldrich), 4-bromomethyl benzoic acid (Aldrich), sodium ascorbate (Acros Organics), copper(II) sulphate anhydrous (Aldrich), and ethylenediaminetetraacetic acid disodium salt dihydrate (Aldrich).

Glutaraldehyde was purchased as a 50 wt% solution in water (Aldrich) and was lyophilised before use.

Chloroform-*d* (99.8% D atom), methanol-*d*4 (99% D atom), dimethyl-sulfoxide-*d*6 (>99.5% D atom) and deuterium oxide (99.9% D atom) were obtained from Aldrich and used as received.

All solvents were obtained from Fisher Scientific and were of HPLC grade and used without purification.

HEK-293T cells were obtained from ATCC and were cultured in Dulbecco's Modified Eagle's Medium (DMEM) for cell culture (Gibco, ThermoFisher) supplemented with foetal bovine serum, L-glutamine and penicillin streptomycin from ThermoFisher. Prior to fluorescent imaging, cells were incubated in Opti-MEM reduced serum medium (Gibco, ThermoFisher). PrestoBlue reagent was purchased from Promega, UK. Phosphate buffered saline (PBS) was obtained from Gibco, ThermoFisher.



## Methods

**NMR spectroscopy.**  $^1\text{H}$  and  $^{13}\text{C}$  NMR spectra were recorded on a Bruker DPX-400 spectrometer using deuterated solvent (materials section).

**Size exclusion chromatography (SEC).** A Polymer Laboratories PL-50 instrument equipped with differential refractive index (DRI) was used for SEC analysis. The system was fitted with  $2 \times \text{PLgel Mixed D}$  columns ( $300 \times 7.5 \text{ mm}$ ) and a PLgel  $5 \mu\text{m}$  guard column. The eluent used was DMF with 0.1% LiBr. Samples were run at  $1 \text{ mL min}^{-1}$  at  $50^\circ\text{C}$ . Poly (methyl methacrylate) standards (Agilent EasyVials) were used for calibration between  $955\,500\text{--}550 \text{ g mol}^{-1}$ . Analyte samples were filtered through a membrane with  $0.22 \mu\text{m}$  pore size before injection. Experimental molar mass ( $M_n$ , SEC) and dispersity ( $D$ ) values of synthesised polymers were determined by conventional calibration using Cirrus Size Exclusion Chromatography (SEC) software.

**Mass spectroscopy (MS).** Mass spectra were recorded on a Bruker MicroTOF spectrometer using electrospray ionisation (ESI). Selected mass-to-charge ratio peaks ( $m/z$ ) are quoted in Daltons.

**Fourier transform infrared (FTIR) spectrometry.** FTIR spectrometry was performed on an Agilent Cary630 FTIR with an attenuated total reflection (ATR) module between the wave-number range of  $4000\text{--}650 \text{ cm}^{-1}$ .

**General procedure for diacid monomer synthesis.** Diacid monomers D1 to D6 were synthesised using the following general procedure adapted from a previously described method.<sup>45</sup> A Michael addition substrate (containing either a primary amine, or two secondary amines) was dissolved in methanol (MeOH) along with 5 equivalents of *tert*-butyl acrylate. The reaction mix was heated to  $45^\circ\text{C}$  and stirred for 24 hours. Following reaction completion, the solvent and excess acrylate were removed under reduced pressure and the product was redissolved in dichloromethane (DCM) then washed three times with brine before being dried over anhydrous magnesium sulphate, filtered and concentrated under vacuum. The *tert*-butyl groups were then removed by dissolving the product in DCM followed by the addition of 8 equivalents of acetyl chloride and 8 equivalents of water. The reaction mix was stirred at room temperature for 18 hours and the solvent and excess reagents were then removed under reduced pressure to yield the desired diacid monomer. Full characterisation data are given in the ESI.†

Monomer D7 was synthesised by mixing 1-(3-aminopropyl) imidazole with 2.4 equivalents of *tert*-butyl acrylate and heating the resultant mixture at  $70^\circ\text{C}$  for 48 hours before removing excess acrylate under vacuum.<sup>46</sup> The *tert*-butyl groups were then removed by the same method as described for monomers D1 to D6, but after removing solvents and reagents under vacuum, the product was redissolved in methanol and precipitated from ice cold diethyl ether, repeated a total of three times to improve the purity. The resultant impure mix containing monomer D7 was used crude in the polymerisation reaction.

**General procedure for A2 B2 Passerini 3-component polymerisation.** Polymers were synthesised following previously reported methodologies.<sup>18</sup> The diacid monomer was dissolved at a concentration of  $1 \text{ mmol mL}^{-1}$  with 1 equivalent of glutaraldehyde in an appropriate solvent, chosen based on monomer solubility (either 9 : 1 DCM/*N,N*-dimethylformamide (DMF), dimethyl sulphoxide (DMSO) or 9 : 1 water : DMF) and the reaction mix was stirred at room temperature for 30 minutes. At this point 2 equivalents of isocyanide was added and the reaction mix was stirred at room temperature for a further 2 days. Polymers were purified by precipitation twice in diethyl ether, or by dialysis against ultra-pure water as appropriate.

**General procedure for thiol/ene functionalisation of D1–I1 and D1–I2.** Following previously reported procedures,<sup>47</sup> alkene functionalised polymer (either D1–I1 or D1–I2) was dissolved in DMF along with 10 equivalents of thiol and 0.55 equivalents of azobisisobutyronitrile (AIBN). The reaction mixture was degassed under nitrogen and then heated to  $80^\circ\text{C}$  for 18 hours. The reaction mix was purified by precipitation from ice cold diethyl ether, repeated a total of 3 times.

For reactions with 2-(dimethylamino)ethanethiol hydrochloride, additional purification was required before precipitation. An excess of pyridine (2 ml per 100 mg of starting material polymer) was added and the reaction mix was stirred for 10 minutes and then filtered before precipitation from ice cold diethyl ether was conducted as before.

**General procedure for copper azide/alkyne click functionalisation of D2–I1, D2–I2 and D2–I3.** Adapting previously reported procedures,<sup>48</sup> alkyne functionalised polymer (D2–I1, D2–I2 or D2–I3) was dissolved in a 1 : 1 mix of DMF/MeOH along with 1 equivalent of azide, 0.45 equivalents of sodium ascorbate and 0.1 equivalents of copper(II) sulphate ( $\text{CuSO}_4$ ). The reaction mix was heated to  $45^\circ\text{C}$  for 24 hours, then diluted with water and dialysed against a 5% w/v solution of ethylenediaminetetraacetic acid disodium salt ( $\text{EDTA-Na}_2$ ) in a 1 kDa cut-off membrane for 24 hours and then dialysed for a further 24 hours against ultra-pure water.

Desired azide compounds were prepared by dissolving an appropriate halide in DMF with 1.3 equivalents of sodium azide and stirring at room temperature for 24 hours. The reaction mix was then poured over ice and extracted three times with DCM. The combined organic phase was dried over magnesium sulphate and concentrated under vacuum.

**Incubation of polymers with HEK-293T cells.** Cells were plated to a 96-well clear flat bottom plate at a cell density of 25 000 cells per well in  $200 \mu\text{L}$  DMEM and allowed to attach for 24 h at  $37^\circ\text{C}$ , 5%  $\text{CO}_2$  in a humidified incubator to reach 90% confluency. After that, growth media was removed. Polymers were dissolved at  $640 \mu\text{g mL}^{-1}$  in 25 mM sodium acetate buffer and then diluted 1 in 10 in Opti-MEM to a final concentration of  $64 \mu\text{g mL}^{-1}$  and  $200 \mu\text{L}$  of polymer/Opti-MEM solution was applied to each well. Cells were incubated for a further 24 hours at  $37^\circ\text{C}$ , 5%  $\text{CO}_2$  in a humidified incubator, then all media was removed, and the cells were gently washed with  $100 \mu\text{L}$  of PBS before imaging.



**Effects of polymers on cell metabolic activity.** Cells were plated and treated as above, but 24 hours after treating the cells, the medium in each well was replaced with 100  $\mu\text{L}$  of 10% PrestoBlue in PBS. After incubation at 37  $^{\circ}\text{C}$  and 5%  $\text{CO}_2$  for 45 minutes, the total volume was transferred to a black 96-well plate and the fluorescence intensity was measured at 560 nm excitation and 590 nm emission to determine the metabolic activity of the cells. Cells treated with 1% Triton X-100 were used as a negative control group, and untreated cells were used as a positive control. Metabolic activity (%) measurement was calculated relative to these two controls.

## Results and discussion

### Monomer design and synthesis

In order to produce a chemically diverse library of synthetic macromolecules, we planned to utilise an A2 + B2 + 2C type P3CP with dicarboxylic acid (A2), dialdehyde (B2) and mono-isocyanide (C) monomers to yield a polyester chain. This combination of reagents results in a polymer chain of alternating units formed from the diacid and the dialdehyde, with pendant amide groups primarily formed from the isocyanide component. To incorporate structural diversity into the resultant polymers, we decided to synthesise a range of novel diacid monomers, which could then be combined with the commercially available dialdehyde glutaraldehyde and a range of isocyanides. We sought to incorporate easily functionalisable handles into several of the monomers to allow for post-modification of the resultant polymers. We hypothesised that we could adapt established Aza-Michael addition chemistries to produce a range of beta-amino diacid monomers, which could be further polymerised with the dialdehyde and isocyanide to produce multicomponent polymers with an ionisable polyester backbone and amide pendant chains.<sup>45</sup>

For the initial monomer synthesis, we produced diacid monomer D1 by an Aza-Michael addition between allylamine with *tert*-butyl acrylate, followed by an acid-mediated deprotection of the *tert*-butyl groups conducted by generating hydrochloric acid *in situ* via the reaction of acetyl chloride ( $\text{AcCl}$ ) with water, which served to unveil the desired diacid moiety. Reaction progress could be followed by  $^1\text{H}$  NMR spectroscopy, showing in the first step the complete conversion of acrylate groups and in the second stage, the complete elimination of the distinctive tertiary-butyl group.

The result was an alkene functionalised pendant group across a  $\beta$ -amino diacid. Following optimisation, this route proceeded under mild conditions, with high yield, and required minimal work-up or purification; the product of each step could be isolated by washing and separation procedures only, with no requirement for intensive procedures like column chromatography or distillation, which makes this chemistry amenable for scale up.

Encouraged by the initial monomer synthesis, we then sought to generate a broader library of starting materials into the monomer synthesis method to adapt the monomer struc-

ture and consequently introduce further functionality into the final polymer. The synthesis pathway proved robust enough that the Aza-Michael addition with *tert*-butyl acrylate proceeded successfully with propargylamine as well as piperazine, *N,N*-dimethylethylenediamine, *N,N'*-dimethylethylenediamine and *N,N',N''*-trimethyldiethylenetriamine. Likewise, the deprotection procedure could also be applied to these new substrates without requiring any modifications, to yield diacid monomers D2–D6. In each case, the combined yield over the two steps ranged from 75–90%. Monomers were characterised by NMR, MS and FTIR; in the same manner as for monomer D1, the formation of each monomer could be tracked by  $^1\text{H}$  NMR spectroscopy, showing the conversion of the acrylate groups following Aza-Michael addition, and elimination of the tertiary-butyl group during deprotection. Following deprotection it was also possible to identify the carboxylic acid moiety by the presence of a broad peak in the FTIR spectrum at approximately 2900–2600  $\text{cm}^{-1}$ . Data can be found in full in the ESI.†

However, Michael addition with 1-(3-aminopropyl)imidazole following this protocol proved unsuccessful; with acrylate  $^1\text{H}$  NMR signals remaining. Instead, it proved necessary to proceed *via* a high-temperature, solvent-free Michael addition as described by Zhao *et al.*<sup>46</sup> The product was then deprotected as described above, but was impure. Partial purification was achieved by precipitating the reaction mix dropwise in ice-cold diethyl ether. The precipitate containing monomer D7 was then dried and used without further purification in subsequent polymerisation reactions.

### Polymerisation

Having produced a library of diacids (D1–7), we then sought to evaluate their ability to participate in an A2 + B2 + 2C P3CP step-growth polymerisation. In the first instance, this was achieved by combining D1 as a model diacid monomer along with a dialdehyde, glutaraldehyde, and a monofunctional isocyanide, tertiary-butyl isocyanide. The isocyanide and dialdehyde monomers were chosen because they are commercially available and functionally simple, so would avoid adding additional synthetic complexity at this stage. In addition, the use of tertiary-butyl isocyanide has previously been well established in Passerini polymerisations.<sup>18</sup> D1 was combined with an equivalent amount of glutaraldehyde, before the addition of two equivalents of tertiary butyl isocyanide (I1), and allowed to react at room temperature for 48 hours, as outlined in Fig. 1. Purification was achieved by repeated precipitation from ice-cold diethyl ether, with no additional work-up required. Following this methodology, P3CP proceeded successfully under ambient conditions and delivered the desired polymer D1–I1 as a brittle, pale yellow solid, in good yield (>90%).

Polymerisation was confirmed by both  $^1\text{H}$  NMR spectroscopy and SEC. The  $^1\text{H}$  NMR spectrum of D1–I1 is shown in Fig. 2. The distinctive multiplet at 4.95 ppm is highly characteristic of the CH group between the ester and amide groups that form *via* the P3CR – in this instance, this correlates with





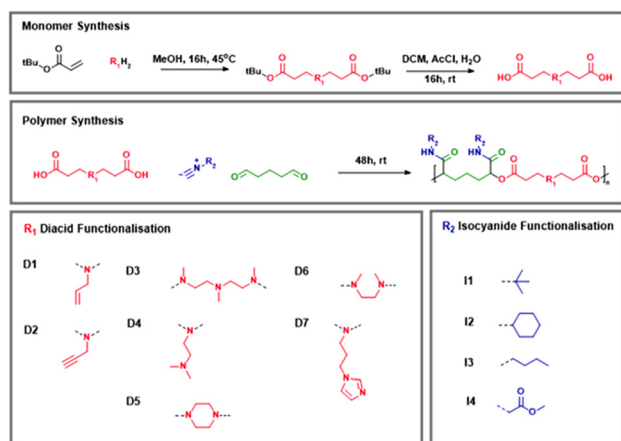


Fig. 1 Strategies for the synthesis of novel diacid monomers and Passerini 3-component reaction derived polymers.

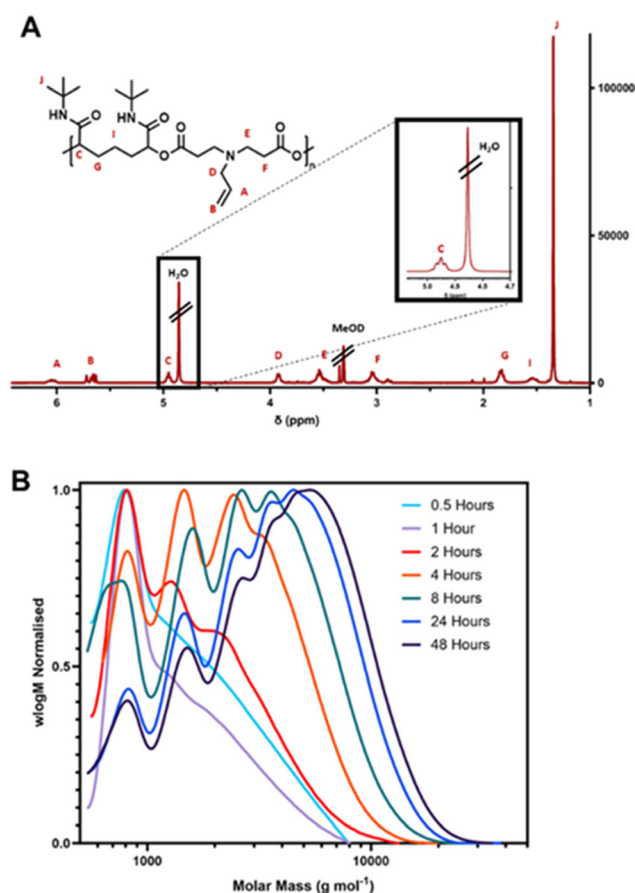


Fig. 2 (A)  $^1\text{H}$  NMR spectrum of Passerini derived polymer D1–I1; (B) DMF-SEC chromatograms of polymer D1–I1 conducted at intervals throughout the synthesis.

the atom labelled C in Fig. 2A. The progress of the reaction was followed by SEC analysis of reaction samples extracted at intervals throughout the course of the reaction (Fig. 2B).

As anticipated for a step-growth polymerisation procedure, initially, we observed the presence of a large number of small oligomers, which appear to be the most prominent peaks in SEC chromatograms up to the 2 hour time point. Over time, these oligomers were replaced with larger polymers, which can be seen by the steady increase in the size of peaks corresponding to higher molecular weights over the next few time points. The molar mass of the polymer increased until it reached a maximum of  $5300\text{ g mol}^{-1}$  at 48 hours, after which, no further increase in molar mass was detected. As a result, all subsequent reactions were stopped after 48 hours.

Whilst the initial polymerisation of D1–I1 was conducted in a 9 : 1 mixture of DCM/DMF, to investigate an alternative solvent system, the polymerisation was also tested in THF. In addition, the polymerisation was conducted at both  $20^\circ\text{C}$  and  $35^\circ\text{C}$  in the DCM/DMF solvent system and at  $20^\circ\text{C}$ ,  $35^\circ\text{C}$  and  $50^\circ\text{C}$  in THF. All other elements of the methodology were unchanged. The reaction proceeded successfully under all five conditions, with the target polymer isolated and characterised by NMR. The length of the resultant polymers was studied *via* SEC, with the results shown below in Fig. 3 and Table 1. The longest polymer chains were obtained from the reactions conducted at  $20^\circ\text{C}$  in DCM/DMF and at  $50^\circ\text{C}$  in THF. However, the THF reaction led to a significantly lower yield (less than half that of the DCM/DMF reaction) and additionally the sample was significantly discoloured; a dark orange colour relative to the pale yellow observed for the product obtained under all the other conditions. For these reasons, the DCM/DMF solvent mix was used for remaining polymerisations unless noted otherwise.

Having established that novel diacid monomer D1 was compatible with Passerini polymerisation, we then expanded the range of materials under investigation. Diacid D2 was introduced first and behaved similarly to D1, and when polymerised with glutaraldehyde and *tert*-butyl isocyanide (I1) led to the synthesis of D2–I1. We then explored the introduction of a wider variety of isocyanide compounds, cyclohexyl isocyanide, *n*-butyl

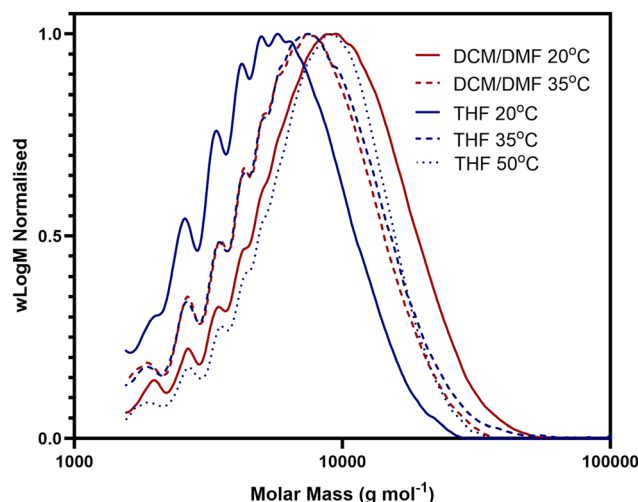


Fig. 3 DMF-SEC chromatograms of polymer D1–I1 synthesised from two different solvents at different temperatures.



**Table 1** Molecular weights and yields for samples of D1–I1 obtained from two solvent systems at different temperatures

Solvent	Temperature	$M_n^a$ (Da)	$\bar{D}^a$	Yield
9 : 1 DCM/DMF	20 °C	7400	1.45	68%
9 : 1 DCM/DMF	35 °C	5800	1.43	56%
THF	20 °C	4300	1.45	45%
THF	35 °C	5700	1.50	57%
THF	50 °C	7200	1.30	30%

<sup>a</sup> Calculated by SEC using 0.05 M LiBr in DMF at 50 °C as the eluent.

isocyanide and methyl isocynoacetate, leading to the successful synthesis of polymers D1–I2, D2–I2, D2–I3 and D2–I4. With cyclohexyl isocyanide and *n*-butyl isocyanide, these reactions proceeded similarly to the tertiary-butyl isocyanide polymerisations and delivered the desired polymers in yields of over 60%, with full purification achieved by precipitation from ice cold diethyl ether, with no changes to the methodology required. However, while polymerisation with methyl isocynoacetate led mainly to the desired product, the polymer could not be fully isolated either by precipitation or dialysis and remained impure.

Polymers were subsequently synthesised from the remaining diacid monomers with tertiary-butyl isocyanide. Diacids D3–D6 were insufficiently soluble in DCM/DMF to proceed with the reaction as originally developed, necessitating a change in solvent. Monomers D3, D5 and D6 proved wholly soluble in deionised water, and polymerisation was conducted in 9 : 1 water/DMF; the addition of DMF assured complete solubilisation of the other monomer compounds and resulted in the greatest polymer chain length relative to the other solvent systems tested. Diacid D4 proved completely soluble in DMSO, and polymerisation was conducted in 100% DMSO, which again resulted in the greatest chain length from the solvent systems tested. Purification of the resultant polymers was conducted not by precipitation, but instead by dialysis against ultrapure water for 24 hours.

Diacid D7 was suitably soluble in DCM/DMF to proceed with polymerisation *via* the original procedure, but to completely purify the polymer, precipitation proved insufficient, and it was again necessary to dialyse the polymer against ultrapure water for 24 hours.

In total, successful reactions with different combinations of diacid and isocyanide monomers led to the synthesis of 11 unique Passerini derived polymers. The range of structures incorporated shows the versatility of the reaction, and the products are anticipated to have a range of different properties resulting from their structural diversity.

The resultant polymers were all characterised by NMR and SEC, and the yields, masses and dispersities ( $\bar{D}$ ) are shown in Table 2 below. Full characterisation data can be found within the ESI.†

### Polymer post-functionalisation

Post-modification of polymers offers an opportunity to incorporate additional functional groups onto the polymer chain,

**Table 2** Passerini 3-component polymerisation derived polymers described in this paper


Polymer	$M_n^a$ (Da)	$\bar{D}^a$	Yield
D1–I1	5000	1.38	92%
D2–I1	4000	1.72	93%
D3–I1	4200	1.22	7%
D4–I1	1900	1.41	5%
D5–I1	1100	1.25	13%
D6–I1	4400	1.22	10%
D7–I1	4500	1.26	7%
D1–I2	2900	1.23	78%
D2–I2	2900	1.41	66%
D2–I3	3500	1.20	69%
D2–I4	3700	1.70	4% (impure)
D1–I1–T1	2400	1.49	41%
D1–I1–T2	2000	1.30	68%
D1–I1–T3	2800	1.41	42%
D1–I1–T4	2400	1.24	17%
D1–I1–T5	4700	1.31	72%
D1–I2–T2	2600	1.51	18%
D1–I2–T4	2900	2.03	61%
D2–I1–A1	4300	1.22	8%
D2–I1–A2	6700	1.31	50%
D2–I1–A3	2800	1.36	39%
D2–I2–A1	3500	1.24	51%
D2–I2–A2	3200	1.34	40%
D2–I2–A3	3700	1.25	62%
D2–I3–A2	2000	1.63	31%

<sup>a</sup> Calculated by SEC using 0.05 M LiBr in DMF at 50 °C as the eluent.

providing a means to modify the properties of the polymers, potentially tailoring them towards desired applications. Post-functionalisation has been applied across polymer science to achieve a wide range of goals, from cross-linking polymers into hydrogels,<sup>49</sup> incorporation of sugar units for interaction with carbohydrate binding sites<sup>50</sup> and the addition of fluorescent labels for polymer imaging.<sup>48</sup> Such modification requires the polymers to possess functional groups that are compatible with further reactions for modification, so monomers D1 and D2 were designed to incorporate alkene or alkyne functional group side chains. These motifs are amenable to post-functionalisation *via* thiol/ene and azide/alkyne click chemistries, and are well tolerated by the P3CP process, so are preserved in the resultant polymer chains. Click chemistries offer simple yet efficient means to modify these handles with a wide variety of different substrates. They offer further benefits as they are typically highly selective and can proceed under mild conditions.<sup>47</sup> Developing click methodologies compatible with our novel polymer system would therefore open up a large amount of chemical space for future expansion of the polymer library.

**Thiol/ene functionalisation.** Our first branch of study was the use of thiol/ene reactions; in this case, a radical addition mechanism converting a thiol and an alkene group into a thioether. As polymers derived from monomer D1 possessed a pendant alkene group, this provided a route to modify the polymers with a broad range of different thiol reagents (Fig. 4A). In the past, thiol/ene reactions have been used mostly to generate crosslinked polymer networks,<sup>51</sup> but more recently they have also been used to introduce a variety of func-



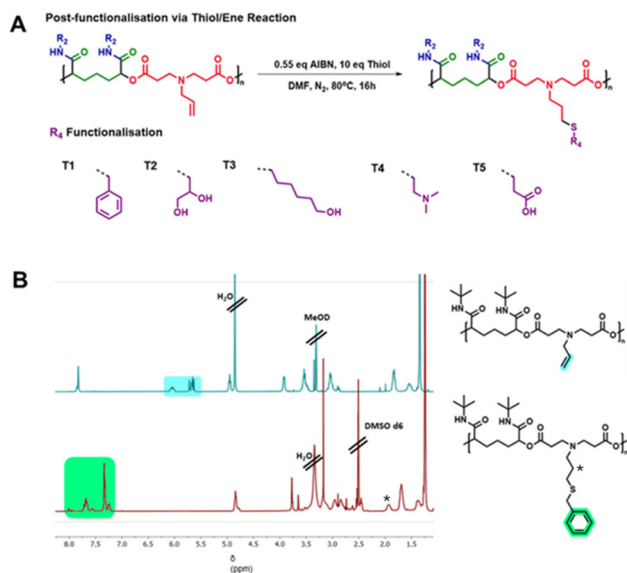

**Fig. 4** (A) Synthesis of post-modified Passerini-derived polymers *via* AIBN-initiated thiol/ene reaction. (B)  $^1\text{H}$  NMR spectra of polymer D1-I1 (top) and the product D1-I1-T1 (bottom) following functionalisation *via* thiol/ene reaction.

tional groups into polymer side chains, with subsequent impacts on molecular properties.<sup>52,53</sup> The thiol/ene reaction is a popular tool for this work, as it proceeds relatively rapidly with a variety of substrates and without the need for metal catalysts.<sup>54</sup>

Passerini derived polymers have previously been shown to be compatible with thiol/ene chemistries and so we investigated a range of techniques to develop a suitable protocol for the modification of our novel polymers derived from diacid monomer D1.<sup>47,55</sup> In reactions between polymer D1-I1 and benzyl mercaptan, thermally initiated coupling using azobisisobutyronitrile (AIBN) proved superior to thermal initiation *via* 4,4'-azobis(4-cyanopentanoic acid) (ACVA), or UV initiation reactions using 2,2-dimethoxy-2-phenylacetophenone (DMPA). Following reaction progression by NMR, we were able to establish reaction completion by the loss of alkene peaks at approximately 5.5–6.0 ppm. We observed that the AIBN reaction reached completion overnight in just one step, whereas the ACVA and DMPA reaction required multiple days along with repeated dosing of both catalyst and thiol for complete conversion of the alkene group. This difference may result from the higher temperatures used for the AIBN reaction, as the polymers synthesised here are significantly sterically hindered and lack torsional flexibility owing to their structure. This rigidity and hindrance may restrict access to the reaction site at lower temperatures. Ultimately, we established an AIBN catalysed procedure that involved combining the alkene functionalised polymer with 10 equivalents of thiol and 0.55 equivalents of AIBN under an inert atmosphere. Reaction progress was followed by NMR (Fig. 4B) and SEC (Fig. S1†), allowing us to observe the complete loss of the alkene peaks (highlighted in

blue) from the polymer, and the presence of the new side chain peaks (highlighted in green). Following the successful thiol/ene reaction, polymers were purified by repeated precipitation from ice-cold diethyl ether.


The initial procedure was developed with benzyl mercaptan, due to the distinctive NMR signature of the benzene ring, which was beneficial for early analysis during the method development. Following success with this model substrate, the same methodology was successfully applied to both polymers D1-I1 and D1-I2 and a range of different thiol substrates, chosen to incorporate a broad range of different functionalities and chemical properties, with each functional group anticipated to have different impacts on polymer properties. This allowed us to develop a small library of thiol/ene functionalised polymers (Fig. 4A), detailed in Table 2. The molecular weight of the polymers as measured by SEC was in many cases observed to decrease following the thiol/ene reaction, this was generally considered to be a result of the changing identity of the polymer side chain impacting behaviour of the polymer within the column, which in turn could impact elution times, although it is also possible that the high temperatures used could have led to some degree of degradation of the polymer chain during the reaction.

**Copper initiated azide/alkyne click.** Subsequently, we sought to introduce copper-initiated azide/alkyne cycloaddition (CuAAC) reactions as a further method of polymer post-functionalisation *via* click-chemistries. CuAAC provides a route to react terminal alkyne groups with azide-containing substrates to yield substituted triazole products, it is highly selective, tolerates a wide range of functional groups and solvents, and is compatible with a wide range of substrates.<sup>56</sup> CuAAC has been widely adopted by polymer chemists for roles including polymer conjugation<sup>57</sup> and polymer functionalisation.<sup>58–62</sup>

We therefore sought to modify the alkyne functionalised polymers derived from monomer D2 by reaction with azide functionalised substrates. Polymer functionalisation was initially tested between polymer D2-I1 and benzyl azide as a test substrate. We utilised a synthetic route that used sub-stoichiometric amounts of copper and regenerated the active species throughout the reaction.<sup>48</sup> In this instance, the polymers were combined with 1 equivalent of azide along with 0.45 equivalents of sodium ascorbate and just 0.1 equivalents of copper sulphate. Polymers were then purified by dialysis against a solution of EDTA disodium salt, and then subsequent dialysis against deionised water, followed by lyophilisation.

Once this protocol was successfully established with D2-I1 and benzyl azide it was then expanded to the remaining D2-derived polymers and other azide substrates (Fig. 5A), once more, these substrates were chosen to test diverse functional groups both for compatibility with the reaction protocol and for impacts on polymer properties. Reaction progress was followed by NMR (Fig. 5B) and SEC (Fig. S2†), allowing us to track completion by observing the complete loss of the alkyne peak (highlighted in blue, Fig. 5B) from the polymer D2-I1. Additionally, the successful formation of the triazole ring



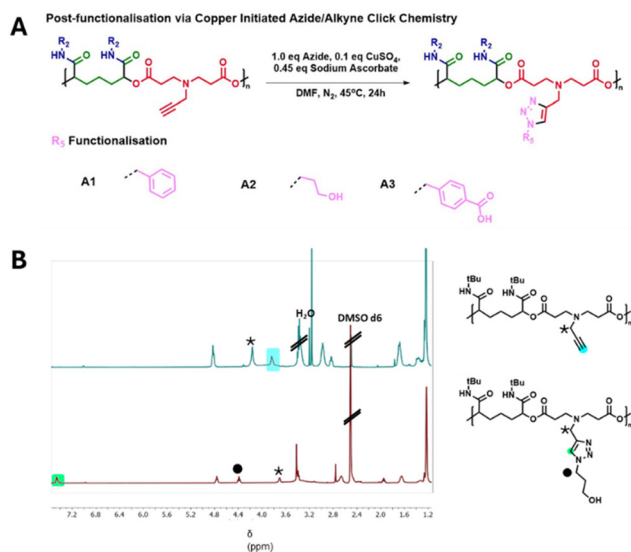

**Fig. 5** (A) Synthesis of post-modified Passerini derived polymers via copper-initiated azide/alkyne click. (B)  $^1\text{H}$  NMR spectra of polymer D2-I1 (top) and the product D2-I1-A2 (bottom) following functionalisation via copper/click chemistry.

could be observed by the presence of the distinctive signal for the triazole proton at approximately 7.3 ppm, which can be seen in Fig. 5B (highlighted in green) for the product D2-I1-A2. FTIR spectra from before and after the reaction show the loss of the alkyne C-H stretch at  $3300\text{ cm}^{-1}$  and C $\equiv$ C stretch at  $2140\text{ cm}^{-1}$  showing conversion of the alkyne group; (Fig. S3†). As before, some of the functionalised polymers were found to differ in apparent molar mass compared to the unfunctionalised starting materials. This could again be the result of the functionalised polymers interacting differently with the SEC column, leading to different elution times.


### Luminescence properties of polymers in intracellular environments

Many synthetic polymers have found applications in biology, from carriers for enhanced delivery of therapeutics,<sup>22</sup> to synthetic extra-cellular scaffolds.<sup>63</sup> In our previous work,<sup>22</sup> we found that amphiphilic Passerini block co-polymers with no charged or reactive groups in their backbone or side chains were well-tolerated in specific cell lines at concentrations up to  $0.5\text{ mg mL}^{-1}$ . However, for the materials in this study, the presence of ionisable amines in the polymer main chains was a potential concern for membrane interaction or cytotoxicity. Consequently, we thought it prudent to test how well human cells, in this case, the widely used HEK-293T cell line, would tolerate the amine-containing Passerini polymers. Initial assays showed that the polymers were not toxic in this cell line (Fig. S4†). However, microscopy investigations revealed that, despite lacking typical chromophores, a number of these polymers induced luminescence in the GFP channel when incubated with the HEK-293T cells. The results of this can be seen in Fig. 6.

Polymeric luminescence without conventional fluorophores is not unprecedented, with studies of PAMAM dendrimers dating back to 2001 which reported unexpected optical properties, and the topic was reviewed in 2019.<sup>64</sup> More recent papers include observation of green fluorescence in poly(ester amides) by Zia *et al.*<sup>65</sup> and an observation of fluorescence arising from peptides without 'conventional' fluorophores from Monti *et al.*<sup>66</sup> In most instances, the occurrence of what has been termed non-traditional intrinsic luminescence (NTIL) has been ascribed to chain-association and confinement phenomena, in a manner similar to aggregation-induced emission (AIE). One common feature is the presence of tertiary amine functionality, and it has also been noted that increasing the rigidity of a potential light-emitting (or lumogenic) unit within a polymeric structure can increase the emission intensity of the material.<sup>67–69</sup> All the polymers in this study contained tertiary amines, and the most emissive, *i.e.* D7-I1 and D2-I1-A1, contained aromatic units, but these were not highly conjugated. Rigidity may have been a factor, as the pendant *t*-butyl groups at the side-chain amides would likely reduce mobility adjacent to these sites, with the effect of 'locking' parts of the polymer main chain in set conformations. Thus, some of the criteria for NTIL are met by these Passerini systems. However, the luminescence phenomena were only observed when the polymers were incubated with cells, suggesting that other components were important in the induction of light emission. To eliminate the possibility of cellular autofluorescence, cells from the same cell line were incubated in the absence of polymer and imaged under the same conditions (Fig. 6I). No light emission was detected under these conditions and so we conclude that the luminescence was due to a combination of the polymers with cellular components rather than the cells or polymers alone. Solutions of a range of polymers were prepared in different aqueous solvents and components of cell media, and the resulting emission profiles were measured. We also tested polymer luminescence in the presence and absence of copper ions, in 25 mM sodium acetate buffer, ultra-pure water, phosphate buffered saline and in OptiMEM reduced serum medium (Fig. S5–S12). In all these cases, no significant luminescence was apparent unless the polymers were internalised in the HEK-293T cells. We also carried out experiments in a different cell line, the triple negative breast cancer MDA-MB-231 line, and again luminescence was observed with the brightest emission from polymer D2-I1-A1 (ESI Fig. S13†). It seems likely that aggregation occurred intracellularly, as evidenced by punctate luminescence in discrete regions in the cellular interiors (ESI Fig. S14†). However, further dye-labelling experiments to determine specific intracellular compartment co-localisation were not able to give unequivocal data owing to the broad band light emission of the polymers. We suggest that macromolecular crowding in regions of the cellular interior may have caused aggregation-induced emission from the polymers. It is well-established that the cytosolic interior is a tightly regulated environment, with high concentrations of biomacromolecules and a fine balance of water and electrolytes. It is also known that under stress conditions, cells can alter processes to reduce damage, including the aggregation of macromolecules in tight





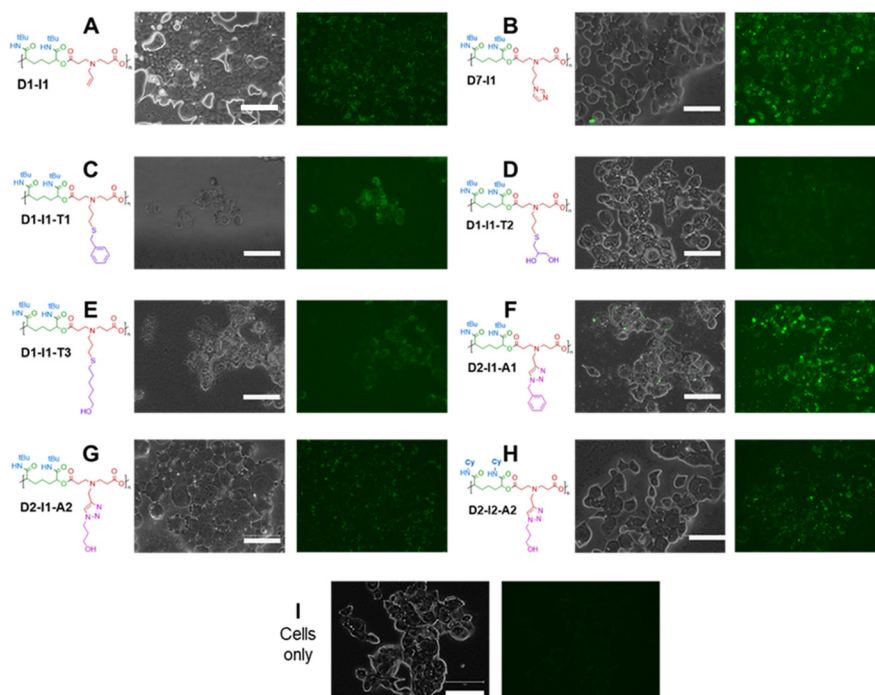

**Fig. 6** Combined brightfield and fluorescence microscopy images (left in each case) and fluorescence channel images (right in each pair), depicting HEK-293T cells incubated for 24 hours with polymers at  $64 \mu\text{g mL}^{-1}$  in OptiMEM reduced serum medium. Fluorescence imaging captured with excitation at 482 nm, emission at 524 nm. (A) D1-I1; (B) D7-I1; (C) D1-I1-T1; (D) D1-I1-T2; (E) D1-I1-T3; (F) D2-I1-A1; (G) D2-I1-A2; (H) D2-I2-A2; (I) cells only (polymer free), media only control. Fluorescence images all enhanced by 10% for contrast to facilitate visualisation. Scale bar =  $75 \mu\text{m}$ .

networks to mitigate dehydration and by formation of ‘stress granules’ with phase-separated regions of nucleic acids and their associated binding proteins.<sup>70</sup> Although we observed no acute toxicities of the polymers in this study, it is possible that the cells in culture did experience temporary osmotic shock on the ingress of the Passerini polymers, and any resulting increase in macromolecular crowding would result in aggregation, and alignment of acylamino, carbonyl and amine groups on adjacent polymer chains. These functional groups have all been reported to generate non-traditional intrinsic luminescence,<sup>71,72</sup> and experiments are now ongoing to establish a detailed mechanism underlying this cell-induced luminescence with these Passerini-type polymers.

## Conclusions

The methods developed here have led to the successful development of a range of novel, modular diacid monomers, which can be polymerised by exploiting Passerini 3-component polymerisation to synthesise a library of novel polymers *via* a robust, efficient procedure. This led to a broad polymer library, which was further enhanced by utilising thiol/ene and azide/alkyne click chemistries to achieve a wide degree of post-functionalisation. Post-functionalisation is anticipated to impact the properties of the polymers, and could be exploited further for a process of rapid, iterative polymer design so that the resultant polymers can be adapted for a wide range of appli-

cations. A large area of chemical space remains untapped in the modification of these polymers and many more substrates could be integrated into the monomer synthesis, polymer synthesis and the post-functionalisation process. Future studies will explore further the use of these materials to label cells without conventional fluorophores.

## Author contributions

Lewis O'Shaughnessy conceptualisation, methodology, validation, formal analysis, investigation, visualisation, writing – original draft. Mariarosa Mazza: conceptualisation, supervision; writing – review & editing; funding acquisition, resources Akosua Anane-Adjei: conceptualisation, supervision, writing – review & editing, funding acquisition, resources Naoto Hori: conceptualisation, supervision, writing – review & editing. Pratik Gurnani: conceptualisation, supervision, writing – review & editing. Cameron Alexander: conceptualisation, supervision; writing – review & editing; funding acquisition, resources.

## Data availability

All data in this paper are included in the ESI.† Other relevant data are available on request *via* University College London,



the University of Nottingham, p.gurnani@ucl.ac.uk or cameron.alexander@nottingham.ac.uk.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

We thank UKRI/EPSCRC for funding [grant EP/S023054/1] and the Royal Society [Wolfson Research Merit Award WM150086 to CA]. We also thank Tom Hyde, Esme Ireson and Paul Cooling for expert technical support. The Nanoscale & Macroscale Research Centre (NMRC) is acknowledged for providing the facilities for TEM and related analysis, and we thank the School of Life Sciences imaging facility (SLIM) and staff for their contribution to this publication.

## References

- H. Liu, P. Kanjilal and S. Thayumanavan, *Polym. Int.*, 2022, **71**, 562–568.
- B. Wei, W. Li, Z. Zhao, A. Qin, R. Hu and B. Z. Tang, *J. Am. Chem. Soc.*, 2017, **139**, 5075–5084.
- R. Kakuchi, *Angew. Chem., Int. Ed.*, 2014, **53**, 46–48.
- S. Kumar, A. Arora, S. Kumar, R. Kumar, J. Maity and B. K. Singh, *Eur. Polym. J.*, 2023, **190**, 112004.
- I. Jesin and G. C. Nandi, *Eur. J. Org. Chem.*, 2019, **2019**, 2704–2720.
- M. Arend, B. Westermann and N. Risch, *Angew. Chem., Int. Ed.*, 1998, **37**, 1044–1070.
- S. Oelmann, A. Travanut, D. Barther, M. Romero, S. M. Howdle, C. Alexander and M. A. R. Meier, *Biomacromolecules*, 2019, **20**, 90–101.
- M. Konstantinidou, K. Kurpiewska, J. Kalinowska-Fluscik and A. Dömling, *Eur. J. Org. Chem.*, 2018, **2018**, 6714–6719.
- A. Sehlinger, O. Kreye and M. A. R. Meier, *Macromolecules*, 2013, **46**, 6031–6037.
- O. Kreye, T. Tóth and M. A. R. Meier, *J. Am. Chem. Soc.*, 2011, **133**, 1790–1792.
- B. Alkan, O. Daglar, S. Luleburgaz, B. Gungor, U. S. Gunay, G. Hizal, U. Tunca and H. Durmaz, *Polym. Chem.*, 2022, **13**, 258–266.
- O. Kreye, O. Türlüç, A. Sehlinger, J. Rackwitz and M. A. Meier, *Chemistry*, 2012, **18**, 5767–5776.
- B. Yang, Y. Zhao, C. Fu, C. Zhu, Y. Zhang, S. Wang, Y. Wei and L. Tao, *Polym. Chem.*, 2014, **5**, 2704–2708.
- R. Kakuchi and P. Theato, *ACS Macro Lett.*, 2014, **3**, 329–332.
- K.-S. Krannig, D. Esposito and M. Antonietti, *Macromolecules*, 2014, **47**, 2350–2353.
- A. Sehlinger, R. Schneider and M. A. R. Meier, *Eur. Polym. J.*, 2014, **50**, 150–157.
- X.-X. Deng, L. Li, Z.-L. Li, A. Lv, F.-S. Du and Z.-C. Li, *ACS Macro Lett.*, 2012, **1**, 1300–1303.
- M. Zhao, N. Liu, R.-H. Zhao, P.-F. Zhang, S.-N. Li, Y. Yue and K.-L. Deng, *ACS Appl. Bio Mater.*, 2019, **2**, 1714–1723.
- A. Sehlinger, P.-K. Dannecker, O. Kreye and M. A. R. Meier, *Macromolecules*, 2014, **47**, 2774–2783.
- S. Saxer, C. Marestin, R. Mercier and J. Dupuy, *Polym. Chem.*, 2018, **9**, 1927–1933.
- A. K. Pearce, A. Travanut, B. Couturaud, V. Taresco, S. M. Howdle, M. R. Alexander and C. Alexander, *ACS Macro Lett.*, 2017, **6**, 781–785.
- A. Travanut, P. F. Monteiro, S. Smith, S. M. Howdle, A. M. Grabowska, B. Kellam, M. A. R. Meier and C. Alexander, *J. Mater. Chem. B*, 2022, **10**, 3895–3905.
- J. Zhang, X.-X. Deng, F.-S. Du and Z.-C. Li, in *Sequence-Controlled Polymers: Synthesis, Self-Assembly, and Properties*, American Chemical Society, 2014, vol. 1170, ch. 15, pp. 223–234.
- X.-W. Kan, X.-X. Deng, F.-S. Du and Z.-C. Li, *Macromol. Chem. Phys.*, 2014, **215**, 2221–2228.
- Y. Cui, M. Zhang, F.-S. Du and Z.-C. Li, *ACS Macro Lett.*, 2017, **6**, 11–15.
- A. Travanut, P. F. Monteiro, S. Oelmann, S. M. Howdle, A. M. Grabowska, P. A. Clarke, A. A. Ritchie, M. A. R. Meier and C. Alexander, *Macromol. Rapid Commun.*, 2021, **42**, 2000321.
- X.-F. Sun, X. Zhang, S.-P. Song, Y.-Q. Yao, Y. Zhang, C.-L. Wang, J.-J. Sun and Q.-F. Wang, *Chin. J. Polym. Sci.*, 2024, **42**, 570–578.
- Y. Zhang, S. Liu and C. Xu, *Polym. Chem.*, 2024, **15**, 2677–2686.
- Y. Nakamura, Y.-S. Huang, C.-F. Huang and S. Samitsu, *Chem. Commun.*, 2024, **60**, 5270–5273.
- Y. Khine, Y. Li, W. Ge and M. H. Stenzel, *Colloid Polym. Sci.*, 2024, DOI: [10.1007/s00396-024-05265-8](https://doi.org/10.1007/s00396-024-05265-8).
- A. Girotti, S. Escalera-Anzola, I. Alonso-Sampedro, J. González-Valdivieso and F. J. Arias, *Pharmaceutics*, 2020, **12**(11), 1115.
- E. Troy, M. A. Tilbury, A. M. Power and J. G. Wall, *Polymers*, 2021, **13**(19), 3321.
- A. Elsherbeny, H. Bayraktutan, U. C. Oz, C. Moloney, J. C. Ashworth, A. M. Grabowska and C. Alexander, *Adv. Ther.*, 2024, **7**, 2300330.
- B. Ballarín-González and K. A. Howard, *Adv. Drug Delivery Rev.*, 2012, **64**, 1717–1729.
- A. Bernkop-Schnürch, *Adv. Drug Delivery Rev.*, 2018, **136–137**, 62–72.
- A. E. Neitzel, G. X. De Hoe and M. V. Tirrell, *Curr. Opin. Solid State Mater. Sci.*, 2021, **25**, 100897.
- H. Bayraktutan, R. J. Kopiasz, A. Elsherbeny, M. Martinez Espuga, N. Gumus, U. C. Oz, K. Polra, P. F. McKay, R. J. Shattock, P. Ordóñez-Morán, A. Mata, C. Alexander and P. Gurnani, *Polym. Chem.*, 2024, **15**, 1862–1876.
- H. Bayraktutan, P. Symonds, V. A. Brentville, C. Moloney, C. Galley, C. L. Bennett, A. Mata, L. Durrant, C. Alexander and P. Gurnani, *Biomaterials*, 2024, **311**, 122647.



- 39 N. K. Dastgerdi, N. Gumus, H. Bayraktutan, D. Jackson, K. Polra, P. F. McKay, F. Atyabi, R. Dinarvand, R. J. Shattock, L. Martinez-Pomares, P. Gurnani and C. Alexander, *Nanoscale Adv.*, 2024, **6**, 1409–1422.
- 40 X. Y. Cai, J. Z. Li, N. N. Li, J. C. Chen, E.-T. Kang and L. Q. Xu, *Biomater. Sci.*, 2016, **4**, 1663–1672.
- 41 K. Kasza, B. Richards, S. Jones, M. Romero, S. N. Robertson, K. R. Hardie, P. Gurnani, M. Cámara and C. Alexander, *ACS Appl. Mater. Interfaces*, 2024, **16**, 5412–5425.
- 42 A. Dömling and I. Ugi, *Angew. Chem., Int. Ed.*, 2000, **39**, 3168–3210.
- 43 R. M. I. Ugi, U. Fetzer and C. Steinbrückner, *Angew. Chem.*, 1959, **71**, 386.
- 44 Z. Zha, J. Li and Z. Ge, *ACS Macro Lett.*, 2015, **4**, 1123–1127.
- 45 N. Suleman, R. S. Kalhapure, C. Mocktar, S. Rambharose, M. Singh and T. Govender, *RSC Adv.*, 2015, **5**, 34967–34978.
- 46 X. Zhao, J. Chen, M. Qiu, Y. Li, Z. Glass and Q. Xu, *Angew. Chem., Int. Ed.*, 2020, **59**, 20083–20089.
- 47 Y.-Z. Wang, X.-X. Deng, L. Li, Z.-L. Li, F.-S. Du and Z.-C. Li, *Polym. Chem.*, 2013, **4**, 444–448.
- 48 A. B. Anane-Adjei, N. L. Fletcher, R. J. Cavanagh, Z. H. Houston, T. Crawford, A. K. Pearce, V. Taresco, A. A. Ritchie, P. Clarke, A. M. Grabowska, P. R. Gellert, M. B. Ashford, B. Kellam, K. J. Thurecht and C. Alexander, *Biomater. Sci.*, 2022, **10**, 2328–2344.
- 49 A. E. Rydholm, C. N. Bowman and K. S. Anseth, *Biomaterials*, 2005, **26**, 4495–4506.
- 50 L. Nurmi, J. Lindqvist, R. Randev, J. Syrett and D. M. Haddleton, *Chem. Commun.*, 2009, 2727–2729, DOI: [10.1039/B904249K](https://doi.org/10.1039/B904249K).
- 51 M. J. Kade, D. J. Burke and C. J. Hawker, *J. Polym. Sci., Part A: Polym. Chem.*, 2010, **48**, 743–750.
- 52 R. L. A. David and J. A. Kornfield, *Macromolecules*, 2008, **41**, 1151–1161.
- 53 A. Gress, A. Völkel and H. Schlaad, *Macromolecules*, 2007, **40**, 7928–7933.
- 54 C. R. Becer, R. Hoogenboom and U. S. Schubert, *Angew. Chem., Int. Ed.*, 2009, **48**, 4900–4908.
- 55 M. Uygun, M. A. Tasdelen and Y. Yagci, *Macromol. Chem. Phys.*, 2010, **211**, 103–110.
- 56 J.-F. Lutz, *Angew. Chem., Int. Ed.*, 2007, **46**, 1018–1025.
- 57 J. A. Opsteen and J. C. M. van Hest, *Chem. Commun.*, 2005, 57–59, DOI: [10.1039/B412930J](https://doi.org/10.1039/B412930J).
- 58 N. Vinson, Y. Gou, C. R. Becer, D. M. Haddleton and M. I. Gibson, *Polym. Chem.*, 2011, **2**, 107–113.
- 59 G. Acik, C. E. Cansoy and M. A. Tasdelen, *J. Appl. Polym. Sci.*, 2019, **136**, 47072.
- 60 B. Pektas, G. Sagdic, O. Daglar, S. Luleburgaz, U. S. Gunay, G. Hizal, U. Tunca and H. Durmaz, *Polymer*, 2022, **253**, 124989.
- 61 N. V. Tsarevsky, K. V. Bernaerts, B. Dufour, F. E. Du Prez and K. Matyjaszewski, *Macromolecules*, 2004, **37**, 9308–9313.
- 62 D. D. Díaz, S. Punna, P. Holzer, A. K. McPherson, K. B. Sharpless, V. V. Fokin and M. G. Finn, *J. Polym. Sci., Part A: Polym. Chem.*, 2004, **42**, 4392–4403.
- 63 H.-Y. Mi, X. Jing and L.-S. Turng, *J. Cell. Plast.*, 2014, **51**, 165–196.
- 64 D. A. Tomalia, B. Klajnert-Maculewicz, K. A. M. Johnson, H. F. Brinkman, A. Janaszewska and D. M. Hedstrand, *Prog. Polym. Sci.*, 2019, **90**, 35–117.
- 65 A. Zia, J. R. Finnegan, J. P. Morrow, W. Yin, J. J. Jasieniak, E. Pentzer, S. Thickett, T. P. Davis and K. Kempe, *Biomacromolecules*, 2021, **22**, 4794–4804.
- 66 A. Monti, C. Bruckmann, F. Blasi, M. Ruvo, L. Vitagliano and N. Doti, *Chem. Commun.*, 2021, **57**, 3720–3723.
- 67 P. K. S. Antharjanam, M. Jaseer, K. N. Ragi and E. Prasad, *J. Photochem. Photobiol., A*, 2009, **203**, 50–55.
- 68 L. Pastor-Pérez, Y. Chen, Z. Shen, A. Lahoz and S. E. Stiriba, *Macromol. Rapid Commun.*, 2007, **28**, 1404–1409.
- 69 X. Liu, Y. Zeng, J. Liu, P. Li, D. Zhang, X. Zhang, T. Yu, J. Chen, G. Yang and Y. Li, *Langmuir*, 2015, **31**, 4386–4393.
- 70 A. Kitamura, S. Oasa, H. Kawaguchi, M. Osaka, V. Vukojević and M. Kinjo, *Sci. Rep.*, 2023, **13**, 11834.
- 71 N. Jiang, Y.-J. Meng, X. Pu, C.-Y. Zhu, S.-H. Tan, Y.-H. Xu, Y.-L. Zhu, J.-W. Xu and M. R. Bryce, *ACS Mater. Lett.*, 2024, 24–31, DOI: [10.1021/acsmaterialslett.4c02100](https://doi.org/10.1021/acsmaterialslett.4c02100).
- 72 N. Jiang, D. Zhu, Z. Su and M. R. Bryce, *Mater. Chem. Front.*, 2021, **5**, 60–75.

