

Straightforward Synthesis of 2- and 2,8-Substituted Tetracenes

Simon Woodward,^{*,[a]} Miriam Ackermann,^[a] Saurabh Ahirwar,^[a] Laurence Burroughs,^[a] Mary Robert Garrett,^[a] John Ritchie,^[a] Jonathan Shine,^[a] Björk Tyril,^[a] Kevin Simpson^[b] and Peter Woodward^[a]


^[a] Prof Dr S Woodward, M Ackermann, S Ahirwar, Dr L Burroughs, Dr M R Garrett, J Ritchie, J Shine, B Tyril, P Woodward, GSK Carbon Neutral Laboratories for Sustainable Chemistry, Jubilee Campus, University of Nottingham, Nottingham NG7 2TU, United Kingdom.

^[b] K Simpson, European Thermodynamics Ltd, 8 Priory Business Park, Kibworth, Leicestershire, LE8 0RX, United Kingdom.

Abstract: A simple regiospecific route to otherwise problematic substituted tetracenes is described. The diverse cores (*E*)-1,2-Ar¹CH₂(HOCH₂)C=C(CH₂OH)I (Ar¹ = Ph, 4-MePh, 4-MeOPh, 4-FPh) and (*E*)-1,2-I(HOCH₂)C=C(CH₂OH)I, accessed from ultra-low cost HOCH₂C≡CCH₂OH at multi-gram scales, allow the synthesis of diol libraries (*E*)-1,2-Ar¹CH₂(HOCH₂)C=C(CH₂OH)CH₂Ar² (Ar² = Ph, 4-MePh, 4-*i*PrPh, 4-MeOPh, 4-FPh, 4-BrPh, 4-biphenyl, 4-styryl; 14 examples) by efficient Negishi coupling. Copper-catalysed aerobic oxidation cleanly provides dialdehydes (*E*)-1,2-Ar¹CH₂(CHO)C=C(CHO)CH₂Ar² which in many cases undergo titanium(IV) chloride induced double Bradsher closure providing a convenient method for the synthesis of regiochemically and analytically pure tetracenes (12 examples). The sequence is typically chromatography-free, scalable, efficient and technically simple to carry out.

Introduction

Of diverse utility in organic electronics^[1] (including light emitting, transistor, sensor and solar cell applications) tetracene (**1aa**, Scheme 1), and its derivatives, must be synthesised^[2] due to the lack of terrestrial sources.^[3] This situation accounts for the 500-fold cost difference between anthracene and tetracene **1aa** (ca. 7 cents/mmol vs. €35/mmol).^[4] We sought a route to **1aa**, and simple derivatives, which fulfilled the following characteristics: (i) minimised total step-count (ii) use of only low cost sustainable starting materials, (iii) diversity orientated intermediates facilitating the preparation of substituted tetracene libraries, (iv) simple (chromatography-free) work-up procedures providing analytically pure intermediates and final tetracenes, (v) applicability to gram scales without yield or purity degradation issues. While many elegant approaches to (substituted) tetracenes (**1**) are known^[2] failures against one or more of the criteria (i)-(v) are unfortunately extremely commonplace. Traditional routes to tetracene derivatives typically involve *unidirectional synthesis* from *ortho* substituted phenylene units wherein only one ring is formed at a time (e.g. C-ring closure in the right of Scheme 1). The nice commercial (3M) process to 2-chlorotetracene of Gerlach is a good example of such a disconnection.^[5] We thought to use *bidirectional synthesis*, a powerful tool in natural product preparation,^[6] but which is rarely used in accessing tetracenes^[7] or indeed polyaromatics^[8] in general.

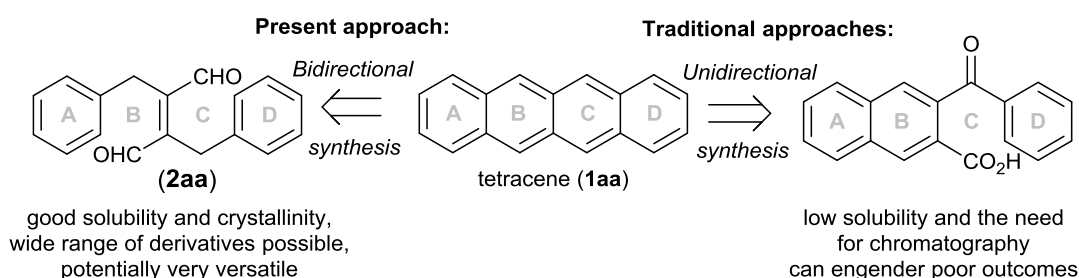


Scheme 1. The approach herein to tetracenes (**1**) using bidirectional^[6] closure (B,C-ring formation) of highly soluble and crystalline *bis*-aldehydes (**2**) vs. an exemplary unidirectional synthesis. Adding substituents to the A/D phenyl groups allows access to acene derivatives.

The proposal on the left of Scheme 1 requires Bradsher^[9] (hydroxyalkylation) closure of both aldehydes in **2** directly forming the B and C rings of tetracenes **1** in a single pot. Such two-directional strategies have no exact precedent in tetracene synthesis as far as we can tell. Naphthalene formation from simple *cis*-1,2-substituted alkene(CHO)(CH₂Ph) fragments (the closest analogue of the required B-ring formation in Scheme 1) is described in a handful of cases.^[10] Less than a dozen papers describe 'one-directional' H⁺/Lewis acid closure of phenylene(CHO)(CH₂Ph) units (the reaction most analogous to the required C-ring closure to tetracene). Anthracenes^[11] and benzo[*g*](iso)quinolones,^[12] a *bis*-naphthothieno[2,3-*d*]thiophene,^[8a] a trinaphthylene^[8b] and one very recent tetracene^[8c] have been prepared this way. Contemporary (2016-17) alternatives have highlighted gold^[13] and Fe(III)^[14] catalysed two-directional syntheses to dihydrotetracenes and various polyaromatics, respectively. However, preparation of some cyclisation precursors can be step/chromatographically intensive in such approaches. Cyclisation promoters for tetracene formation in particular need careful selection: H⁺ is commonly used to instigate Bradsher reactions,^[8,9] but such conditions can also readily oxidise the tetracene products to unstable radical cations (that are known to subsequently decompose to complex mixtures).^[15] The use of Lewis acid cyclisation is preferred, but in some cases even these are overly oxidising towards tetracenes.^[16] However, if such issues are overcome core **2** is an attractive precursor for tetracene library synthesis as no post-cyclisation C-oxidation state manipulation is required (c.f. quinoid and dihydrotetracene routes to tetracenes^[2]), water being formally the only by-product produced in the Bradsher aromatisation.

Results and Discussion

We proposed that all of the carbons in our tetracene synthesis should arise from low cost and sustainable 2-butyne-1,4-diol (4 cents/g)^[4] and benzyl chloride (3 cents/g)^[4] or its simple derivatives via the diversity orientated iodides **3-4** (Table 1). Copper-catalysed (CuBr·SMe₂, 2 mol-%) direct addition of 4-(R¹)C₆H₄CH₂MgCl to HOCH₂C≡CCH₂OH proceeds, under our modified literature conditions, to the expected (-OMgCl directed^[17]) (*E*)-carbomagnesiation intermediate which smoothly intercepts iodine providing the new diversity cores **3a-d** (see Supporting Information). Acceptable to good (58-72%) yields, on 10 g scales, are attained by direct crystallisation of the crude reaction products. In the case of **3c**, removal of a Wurtz by-product is necessary prior to recrystallization but this too is straight forward, even at multi-gram levels. Increasing the carbomagnesiation reaction temperature to 50-55 °C is the key to attaining high conversion in these carbocuprations of lower reactivity benzylic Grignard reagents.^[17] Equally conveniently, **4** directly precipitates as an off-white solid from a simple reaction of 2-butyne-1,4-diol with iodine in CHCl₃ on >10 g scales (90% yield), using our modified conditions.^[18] The simplicity of the preparations of **3-4** has encouraged us regarding their commercial availability.^[19]


Iodides **3-4** are potent precursors for straightforward Negishi-type couplings providing **5** efficiently and quickly (Table 1). Previously, slow addition techniques and specialist ligands have been necessary to avoid competitive deprotonation in such unprotected alcohol substrates.^[20] However, this is not the case for **5** and a wide range of asymmetric diols can be realised in excellent yields (85-99%) using a typical *S*-Phos biaryl ligand.^[20] Simple non-proprietary tricyclohexylphosphine (PCy₃) also provides equivalent yields (in all cases tested, Method I). These catalytic Negishi couplings show very strong ligand inhibition at L/Pd ratios of >1 but use of a slight deficiency of phosphine in the coupling prevents this becoming an issue. Isolation of the diols **5** is facilitated by their low solubility in Et₂O, typically trituration in this solvent provides off-white solids (>98% pure) that can be used directly in subsequent transformations. Acetonitrile can be used to similar effect. Finally, the diols **5** are often highly crystalline and frequently attained as glinting colourless analytically pure needles from simple hot MeOH:EtOAc mixtures. By appropriate combination of **3** and benzyl zinc reagent the symmetric diols may also be readily achieved (i.e. **5aa** is attained from **3a** and PhCH₂ZnCl in 87% yield). Alternatively, the symmetrical diols can also be attained from **4** and slight excesses of the appropriate benzylic zinc reagent (Method II). While the scope of this symmetrical coupling is not quite as wide as that from use of **3a-d** (e.g. preparation of **5bb** by Method II provides only 56% vs. 93% via method I) it does allow routine access to the symmetrical diols quickly. For example, **5aa** could be prepared on a >10 g scale by such approaches within a day.

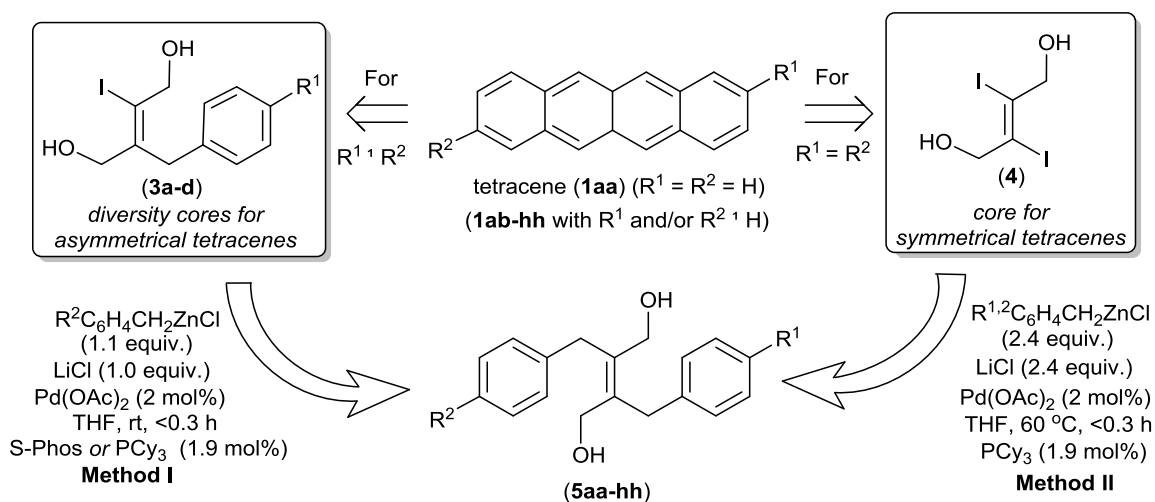Table 1. Diversity orientated synthesis of the diol tetracene precursors **5**.^[a]

Iodide used	Method	R ¹	R ²	Diol	5 (%)	Recrystallisation from ^b	m.p. (°C)
3a	I	H	H	5aa	87	1:1 MeOH/AcOEt	157-158
4	II	H	H	5aa	62-72	-	-
3a	I	H	Me	5ab	84	1:1 MeOH/AcOEt	150-151
3a	I	H	OMe	5ac	91	3:1 EtOAc/MeOH	131-132
3a	I	H	F	5ad	82	1:1 MeOH/AcOEt	139-140
3a	I	H	Ph	5ae	99	1:1 MeOH/AcOEt	154-155
3b	I	Me	Me	5bb	93	1:1 MeOH/AcOEt	180-181
4	II	Me	Me	5bb	56	-	-
3b	I	Me	<i>i</i> Pr	5bf	87	1:1 MeOH/AcOEt	155-156
3b	I	Me	vinyl	5bg	96	<i>i</i> PrOH, -20 °C	161-164
3b	I	Me	Br	5bh	92	1:1 MeOH/AcOEt	153-154
3c	I	OMe	Me	5cb	93	3:1 EtOAc/MeOH	131-132
3c	I	OMe	OMe	5cc	85	MeCN, -20 °C	145-146
3c	I	OMe	F	5cd	85	3:1 EtOAc/MeOH, -20 °C	119-120
3d	I	F	F	5dd	82	MeCN, -20 °C	129-130
4	II	Br	Br	5hh	65	MeCN, -20 °C	139-140

^[a] Typically reactions were carried out on ca. 6 mmol scales in THF (25 mL) over 15-20 min. Recrystallisation from refluxing solvent on cooling to 4 °C unless indicated otherwise.

Oxidation of diols **5** to the aldehydes **2** is necessary prior to tetracene cyclisation (Scheme 1). This is sustainably attained by the aerobic Cu^I/TEMPO-based catalysts (Table 2), optimised by Stahl,^[21] so that use of environmentally unsustainable stoichiometric oxidants is avoided. The slightly modified oxidation procedure used herein shows useful functional group tolerance: both C-Br and styryl functions are preserved even though oxidation procedure is radical driven.^[21] Conveniently these oxidations are self-indicating: initiation of the catalyst commensurate with the immediate appearance of a dark orange-brown colour which becomes emerald green on completion of the oxidation (0.3-1 h). After isolation and drying under vacuum the diols **2** are attained as bright yellow solids in high yield and >98% purity allowing their direct use for immediate tetracene synthesis without any further purification. However, all are also easily recrystallized as glinting yellow flakes from *i*PrOH or *i*PrOH:EtOAc mixtures. Oxidation of the diols **5** at a gram scale is straightforward and further scale-up not an issue: e.g. **2aa** could be attained on a 4 g level without the need for any chromatographic separations. Minor modification of the reaction temperature (to 40 °C) is necessary for diol **5ae** to ensure full solubility and completion of reaction.

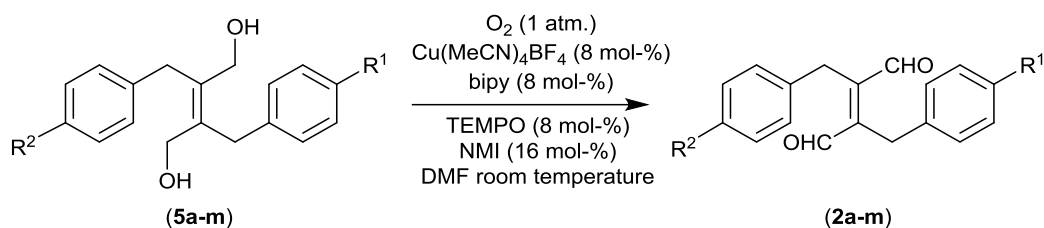
Table 2. Copper(I)-catalysed oxidation of diols **5** to aldehydes **2**.^[a]

5 used	R ¹	R ²	2 (%)	5 used	R ¹	R ²	2 (%)
5aa	H	H	>99	5bg	Me	vinyl	87
5ab	H	Me	87	5bh	Me	Br	98
5ac	H	OMe	88	5cb	OMe	Me	95
5ad	H	F	92	5cc	OMe	OMe	>99
5ae	H	Ph ^[b]	96	5cd	OMe	F	85
5bb	Me	Me	93	5dd	F	F	89
5bf	Me	<i>i</i> Pr	89	5hh	Br	Br	93

^[a] Typically reactions were carried out on ca. 3 mmol scales in DMF (18 mL) over 1 h.

^[b] Reaction at 40 °C.

Preliminary small scale Bradsher closure trials of dialdehyde **2aa** with a library of 14 Lewis acids (Scheme 2, **LA**, see also Supporting Information) revealed that only In(OTf)₃, BF₃·OEt₂ and TiCl₄ were active towards tetracene (**1aa**) formation (Scheme 2). Therefore, these three promoters were all examined in detail. For In(OTf)₃ (at 0.6 equivalents) significant conversion to the desired tetracene **1aa** could only be achieved by prolonged heating at 83-115 °C (Supporting Information); the rate was insufficient for lower catalyst loadings to be viable at practical scales (necessary for viable use of such a poorly sustainable **LA** promoter). Two additional products: **6aa**^[22] and **7aa**^[13,23] (Scheme 2) could also be detected in these indium-promoted closures by comparison with their published ¹H NMR data (independent samples of **6aa** can be prepared by much less efficient alternate chemistry^[22]). Monitoring the reaction by ¹H NMR spectroscopy also confirmed that **6aa** is a genuine ‘half closure’ intermediate on route to tetracene **1aa**.

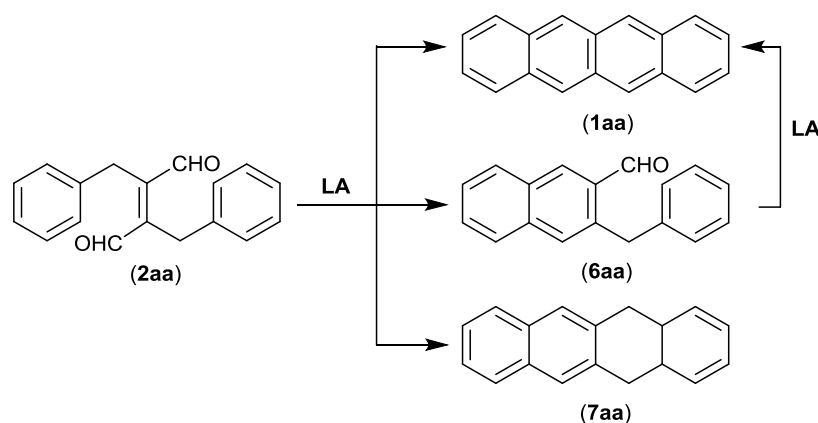
**Scheme 2.** An intermediate (**6aa**) and by-product (**7aa**) in Bradsher closures of aldehyde **2aa** to tetracene (**1aa**).

Stoichiometric BF₃·OEt₂ is much more attractive reagent for tetracene formation due to its low cost. With two equivalents of BF₃·OEt₂ at scales below 1 mmol (in **2aa**), good yields (>80%) of tetracene **1aa** are attained at 1,2-dichloroethane reflux (83 °C) conditions within 5 h. Unfortunately, at larger scales (especially >3 mmol) these reactions become capricious, progressively less clean (with increasing scale) and result ultimately in negligible or no yields of **1aa**. The water by-product of the Bradsher cyclisation is the cause of these issues. Efficiently minimised in small scale reaction mixtures by 1,2-dichloroethane azeotrope formation (b.p. 70.5 °C), in larger scale reactions water promoted H[HOBf₃]^[24] formation competes leading to acid-induced oxidation of **1aa**^[15,24] providing **7aa** (among many other radical cation

derived by-products). Control studies support this idea: deliberate addition of water (2 equiv.) to the reaction mixture at the outset, prior to $\text{BF}_3 \cdot \text{OEt}_2$ (2.0 equiv.) addition and subsequent reflux, leads to catastrophic reduction in the **1aa** yield regardless of the scale of the reaction. Deployment of 4Å molecular sieves in the reaction headspace allows production of **1aa** at a gram scale, but initiation of the cyclisation then becomes slow and equally capricious. Kinetic study of the $\text{BF}_3 \cdot \text{OEt}_2$ promoted cyclisation of **2aa** (0.28 M) provides insights into these behaviours (see ESI[†]). Formation of **1aa** (and disappearance of **6aa**) follow an autocatalytic rate law over 4 h at 63 °C. Dial **2aa** is rapidly converted to **6aa** under these conditions, and fitting standard autocatalysis rate law forms^[25] to the disappearance of **6aa** provides $k_1 \sim 0 \text{ min}^{-1}$ and $k_2 = 0.3 \text{ M}^{-1} \text{ min}^{-1}$ where k_1 and k_2 are respectively estimates of the background and autocatalytic behaviour (see Supporting Information). This strong autocatalysis is the root cause of the reliability issues in larger scale preparations of **1aa** using $\text{BF}_3 \cdot \text{OEt}_2$. Controlling the reactive $\text{H}[\text{HOB}(\text{F}_3)]$ concentration simply becomes impractical at any significant scale in **2aa**. By using only one equivalent of $\text{BF}_3 \cdot \text{OEt}_2$ high yields of **6aa** could be obtained at room temperature, again confirming it as an intermediate en route to **1aa**. In 2015 the syntheses of three tetracenes using a $\text{BF}_3 \cdot \text{OEt}_2$ promoted (unidirectional) Bradsher process were disclosed.^[11c] The colours described for these acenes (colourless to pale green) are not in accord with tetracene formation (which are all typically all brilliant orange). We believe the potential for decomposition effects during the reaction/workup of these reactions similar to the effects observed herein cannot be excluded.

In an attempt to overcome the reproducibility issues associated with $\text{BF}_3 \cdot \text{H}_2\text{O}$ autocatalysis we also screened the little used, low cost, TiCl_4 Bradsher conditions of Tius (Method III, Table 3).^[10c] To our great delight quench (of the most unpromising brown-green reaction mixtures) with 1:1 methanol:acetone resulted in spectacular orange precipitates of **1aa**. Despite the small particle size of the **1aa** produced, very easy filtration is facilitated by use of Whatman glass microfiber filter paper (GF/A which is designed to collect particles sized down to 1.6 μm efficiently). The TiCl_4 approach proved rather general for cyclisation of aldehydes **2**, subject to the usual electronic effects on electrophilic aromatic substitution (Table 3). Partial closure products **6** could often be seen from the filtrates, especially when the donor/acceptor properties of R^1/R^2 were different. The initially precipitated tetracenes **1** are attained in purities (>95%) sufficient for immediate subsequent synthetic/materials application uses. Simple one-step sublimation (200-230 °C, 0.1-0.2 mbar, 1 h) easily provides analytically pure materials as brilliant orange microcrystals. For electronically deactivated dialdehydes (e.g. **2ad**) the use of larger excesses of TiCl_4 (4 equiv.) under neat reaction conditions and longer reaction times (typically 2 days) are required and low to modest yields are attained with these general conditions. Conversely, activated **2bg** was extensively cross-linked on reaction with even one equivalent TiCl_4 at room temperature providing an insoluble orange macromolecular material. Repeating this synthesis at -78 to -40 °C provides oligomeric **1+6bg_n** with $n \sim 7-8$ through controlled polymerisation of the vinyl side chain and mixed mono and di-Bradsher closure. For both the oligo and macromolecular **1+6bg** characteristic tetracene spectroscopic bands can be identified in their UV-vis and IR spectra. Interestingly the monomeric tetracenes **1** all show intense refractive index matching in diamond anvil ATR-IR instruments. The resulting anomalous dispersion leads to the observation of apparent negative peaks around the diamond absorbance range (2100-2000 cm^{-1}) which are a useful quick diagnostic for **1** (even in mixtures), especially if a diagnostic peak at $\sim 905 \text{ cm}^{-1}$ is also present. In line with this suggestion, no pseudo emission peaks are seen using Ge-crystal ATR instruments.

Table 3. Method III: titanium(IV) chloride induced Bradsher cyclisations.^[a]

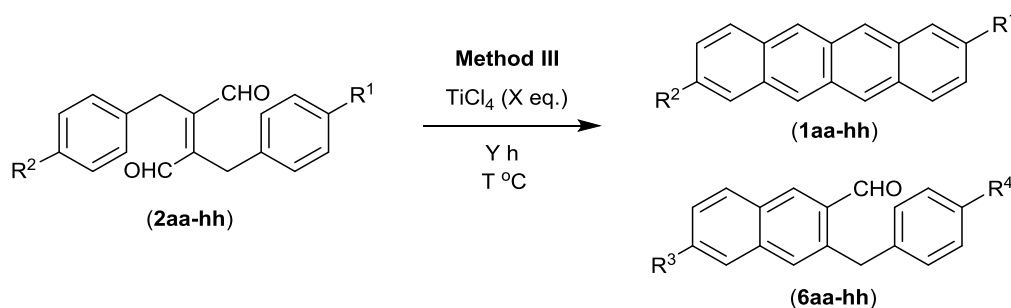

2 used	R^1	R^2	X (eq.)	Y (h), T (°C)	1 (%)	Lit. 1 % ^[b]	Ref.	6 (%)	R^3	R^4
2aa	H	H	2	3 (40)	72	51 (3)	26	-	-	-
2aa	H	H	2	2 (40)	40	-	-	6aa (50)	H	H
2ab	H	Me	2	3 (40)	68	4 (1)	27	-	-	-

2ab	H	Me	2	1 (22)	27	-	-	6ab (57)	Me	H
2ac	H	OMe	2	3 (40)	56 ^[c]	88 (4)	28	-	-	-
2ad	H	F	4	60 (22)	9	56 (3)	29	6ad (37)	H	F
2ae	H	Ph	2	3 (40)	71	-	30	-	-	-
2bb	Me	Me	2	3 (40)	86	low (2)	31	-	-	-
2bf	Me	<i>i</i> Pr	2	3 (40)	86	-	-	-	-	-
2bg	Me	vinyl	2	Note [d]	62	-	-	1+6bg_n (65-89)	Oli ^[e]	Oli ^[e]
2bh	Me	Br	4	60 (22)	4	-	-	6bh (45)	Me	Br
2cb	OMe	Me	2	3 (40)	81	-	-	-	-	-
2cc	OMe	OMe	2	3 (40)	86	-	-	-	-	-
2cd	OMe	F	4	60 (22)	8	-	-	6cd (39)	OMe	F
2dd	F	F	4	60 (22)	trace	-	-	6dd (63)	-	-
2hh	Br	Br	4	60 (22)	-	31 (3)	32	6hh (54)	Br	Br

^[a] Typically reactions carried out on 1.5 mmol scales in 1,2-dichloroethane (10 mL); TiCl₄ added at 0 °C, and the mixture stirred at the required temperature. Electronically deactivated substrates (**ad**, **cd**, **dd**, **hh**) were run in neat TiCl₄ (see ESI[†]).

^[b] The highest/best analogous literature (substituted)tetracene procedure we could identify and (in parentheses) the number of steps needed to prepare the required precursor from commercial (<0.1£ mmol⁻¹) materials.

^[c] Higher solubility limits precipitated yield.

^[d] Reactions carried out at 22 °C afford a low solubility high polymer containing both tetracene and aldehyde groups. Reaction at -78 to -40 °C leads to a soluble oligomer.

^[e] ‘Oli’ indicates product is a (CHCH₂)_n oligomer with n ~ 7-8 generated by polymerisation of the vinyl sidechain providing a telechelic oligomer with both tetracene and aldehyde pendant groups present (see Supporting Information).

Conclusions

The synthetic sequence to **1** from the iodides **3-4** constitutes an effective and practical route for the formation of 2- and 2,8-substituted tetracenes in high analytical purities atypical to most other literature approaches. All of the tetracenes **1** prepared showed the expected spectroscopic properties and have solubilities in CH₂Cl₂ ranging from ca. 10⁻⁶ M (**2bh**) to ~10⁻³ M (**2ac** and fluorine containing tetracenes). The lower solubilities, in part, account for the success of our direct precipitation work-up strategy. From Table 3 it is clear that the approach described herein is complimentary, and in the case of electron-rich substituted tetracenes, advantageous to existing methodology. In particular, the ability to prepare tetracene libraries of various substituents at significant scales quickly and without the use of chromatography is attractive for their subsequent use in materials science at larger preparative scales. The electronic properties of the tetracenes attained are also in line with predictions. For example, 2-methyltetracene (**2ba**) shows an measured E_g(opt) of 2.50 eV which is close to the calculated HOMO-LUMO gap by time dependant DFT of 2.76 eV [CAMB3LY-6-31G(d,p) level of theory] and the accepted value for the parent **1aa** (2.61 eV) [E_g(calc) is typically greater than E_g(opt), see Supporting Information]. For the tetracenes prepared herein we could control E_g(opt) in the range 2.54-2.43 eV by substituent effects. Such ability to easily and systematically vary the HOMO and LUMO energies of tetracenes are central to their use in organic electronic applications and the approach herein simplifies the synthetic effort required to enact the required substituents at useful scales in many cases.

Experimental

Representative example 2-isopropyl-8-methyltetracene (1bf): Prepared from 2-(4-Isopropylbenzyl)-3-(4-methylbenzyl)fumaraldehyde **2bf** (403.1 mg, 1.26 mmol) by treatment with TiCl₄ (0.29 mL, 2.62 mmol, 2.1 eq) in 1,2-dichloroethane (8.5 mL) at 40 °C (3 h). Quenching the green reaction mixture with methanol/acetone (1:1, 10 mL) yielded **1bf** as an orange powder (308 mg, 1.08 mmol, 86%) which could be sublimed (215-225 °C, 0.1 mbar) affording a brilliant orange powder. **M.p.** >250 °C; **UV/Vis** (CH₂Cl₂, 10⁻⁵ M): λ_{max}/nm 475, E_g(opt) 2.49 eV; **¹H NMR** (500.1 MHz, CS₂ external DMSO-d₆ lock): δ 8.18 (s, 1H, H-5), 8.17(5) (s, 1H, H-11), 8.15 (s, 1H, H-12), 8.12 (s, 1H, H-6), 7.57 (d, *J* = 9.0 Hz, 1H, H-4), 7.56 (d, *J* = 8.9 Hz, 1H, H-10), 7.38 (s plus unresolved *meta* coupling, 1H, H-1), 7.37 (s plus unresolved *meta* coupling, 1H, H-1), 6.97, (dd, *J* = 8.9, 1.5 Hz, 1H, H-3), 6.89 (dd, *J* = 8.8, 1.3 Hz, 1H, H-9), 2.79 (sept, *J* = 6.9 Hz, 1H, H-1'), 2.28 (s, 3H, H-1''), 1.15 (d, *J* = 6.9 Hz, 6H, H-2''); **¹³C NMR** (124.7 MHz, CS₂, external DMSO-d₆ lock): δ 143.8 (C), 133.4 (C), 131.0 (2 × C overlap), 130.1 (C), 129.7 (C), 129.6 (C), 129.5 (C), 127.9 (CH), 127.7 (CH), 127.5

(CH), 125.9 (CH), 125.4 (CH), 125.3(5) (CH), 123.3 (CH), 125.1 (CH), 124.7 (CH), 122.9 (CH), 34.1 (CH), 23.1 (CH₃), 21.8 (CH₃); **MS** (+EI) 284 (M); **Anal**: Calcd. for C₂₂H₂₀ C, 92.91; H, 7.09; found C, 92.65; H, 7.18%. Full details for the preparation of **1-7** and their properties are given in the Supporting Information.

Acknowledgments


This work was initiated under funding from the European Union's Seventh Programme for research, technological development and demonstration under grant agreement No 308768. One of us JR is grateful to European Thermodynamics Ltd and the Engineering Physical Sciences Research Council (EPSRC) for provision of a studentship. SW, LB and JR thank EPSRC's National Service for Computational Chemistry (NSCCS) for computational facilities until its closure in 2017. MA thanks the Swiss-European Mobility Programme (SEMP) and is grateful to Prof Steve Howdle and Ms Liv Monaghan for advice and help with GPC analyses. MRG is grateful for the award of an Appalachian College Association Fellowship for sabbatical leave support from Berea College, Kentucky, USA. We are indebted to Dr Callum Welsh (University of Nottingham) and Prof Jens Pflaum (Universität Würzburg) for helpful discussions on refractive index matching and anomalous dispersion effects in diamond anvil ATR-IR spectroscopic studies of tetracenes. We thank Dr Magdalena Foreiter for sample collaboration with Key Organics Ltd and Nottingham Research Chemicals.

Footnotes and References

- [1] Key overviews of tetracene, and other acenes, in organic electronic applications: (a) M. Bendikov, F. Wudl, D. F. Perepichka, *Chem. Rev.* **2004**, *104*, 4891-4946; (b) J. E. Anthony, *Chem. Rev.* **2006**, *106*, 5028-5048.
- [2] Key overviews of tetracene, and other acene, synthetic strategies: (a) H. Qu, C. Chi, *Cur. Org. Chem.* **2010**, *14*, 2070-2108; (b) M. Watanabe, K.-Y. Chen, Y. J. Chang, T. J. Chow, *Acc. Chem. Res.* **2013**, *46*, 1606-1615; (c) R. Dorel, A. M. Echavarren, *Eur. J. Org. Chem.*, **2017**, 14-24.
- [3] Tetracene is a member of the family of poly aromatic hydrocarbons (PAH) which are responsible for the IR emission detected from numerous galactic and extragalactic objects: (a) L. J. Allamandola, D. M. Hudgins, S. A. Sandford, *Astrophys. J.*, **1999**, *511*, L115-L119; (b) A. Candian and P. J. Sarre, *MNRAS*, **2015**, *448*, 2960-2970.
- [4] Direct cost comparison for gramme quantities of 97-98% purity material as supplied by Sigma-Aldrich, April 2017.
- [5] C. P. Gerlach, F. B. McCormick, *U.S. Patent* 20060105199 [3M Innovative Properties Company, USA], 2006, pp. 17 [*Chem. Abs.* **2006**, *144*, 477358]. The vast majority of the approaches of ref. 2 are also unidirectional.
- [6] S. R. Magnuson, *Tetrahedron* **1995**, *51*, 2167-2213.
- [7] Two-directional elaboration of *bis*-benzynes precursors, in the seminal work of Hart and Gribble and the 2014 contribution of Krische were identified: (a) A. Sy, H. Hart, *J. Org. Chem.* **1979**, *44*, 7-9; (b) G. W. Gribble, R. B. Perni, K. D. Onan, *J. Org. Chem.* **1985**, *50*, 2934-2939; (c) L. M. Geary, T.-Y. Chen, T. P. Montgomery, M. J. Krische, *J. Am. Chem. Soc.* **2014**, *136*, 5920-5922.
- [8] We could identify the closure of a 2,5-dibenzyl-3,6-diformyl-thieno[3,2-b]thiophene under acid catalysis to a 6,6,5,5,6,6 ring system in undisclosed yield as one near analogue: (a) J. Il Park, E. J. Jung, S. Y. Lee, *U.S. Patent* 20090043113 [Samsung Electronics Co. Ltd., South Korea], 2009, pp. 14 [*Chem. Abs.* **2009**, *150*, 20093]; one tri-directional synthesis: (b) N. Saino, T. Kawaji, T. Ito, Y. Matsushita, S. Okamoto, *Tetrahedron Lett.* **2010**, *51*, 1313-1316 and one tetracene in a wider recent study: (c) T. Fujita, I. Takahashi, M. Hayashi, J. Wang, K. Fuchibe, J. Ichikawa, *Eur. J. Org. Chem.* **2017**, 262-265.
- [9] C. K. Bradsher, *Chem. Rev.* **1987**, *87*, 1277-1297.
- [10] (a) J. N. Chatterjea, S. K. Roy, *J. Indian Chem. Soc.*, **1957**, *34*, 155-162. (b) M. P. Reddy, G. S. K. Rao, *J. Org. Chem.*, **1981**, *46*, 5371-5373; (c) M. A. Tius, J. Gomez-Galeno, *Tetrahedron Lett.* **1986**, *27*, 2571-2574; (d) M.-R. Tsai, T.-C. Hung, B.-F. Chen, C. C. Cheng, N.-C. Chang, *Tetrahedron*, **2004**, *60*, 10637-10644.
- [11] (a) X. Yu, X. Lu, *Ad. Synth. Catal.*, **2011**, *353*, 569-574. (b) Y. Kuninobu, T. Tatsuzaki, T. Matsuki, K. Takai, Kazuhiko, *J. Org. Chem.* **2011**, *76*, 7005-7009. (c) S. M. Rafiq, R. Sivasakthikumar, J. Karunakaran, A. K. Mohanakrishnan, *Eur. J. Org. Chem.* **2015**, 5099-5114.
- [12] (a) A. P. Krapcho, T. P. Gilmor, *J. Heterocyclic. Chem.* **1998**, *35*, 669-674; (b) A. P. Krapcho, T. P. Gilmor, *J. Heterocyclic. Chem.* **1999**, *36*, 445-452.
- [13] R. Dorel, P. R. McGonigal, A. M. Echavarren, *Angew. Chem., Int. Ed.* **2016**, *55*, 11120-11123.

- [14] C. C. McAtee, P. S. Riehl, C. S. Schindler, *J. Am. Chem. Soc.* **2017**, doi: 10.1021/jacs.7b01114
- [15] P. A. Malachuk, L. S. Marcoux, R. N. Adams, *J. Phys. Chem.* **1966**, *70*, 2064-2065.
- [16] A. S. Dworkin, L. L. Brown, A. C. Buchanan, G. P. Smith, *Tetrahedron Lett.* **1985**, *26*, 2727-2730.
- [17] Y. Ishino, K. Wakamoto, T. Hirashima, *Chem. Lett.* **1984**, 765-768. These room temperature conditions are inefficient for benzylmagnesium chlorides, higher temperatures (50-60 °C) are needed for high yield transformation within 1-2 h.
- [18] L. Luo, D. Resch, C. Wilhelm, C. N. Young, G. P. Halada, R. J. Gambino, C. P. Grey, N. S. Goroff, *J. Am. Chem. Soc.* **2011**, *133*, 19274-19277.
- [19] Compounds **3a-c** and **4** (gram quantities) are available at from Key Organics (www.keyorganics.net) via their Nottingham Research Chemicals range. A range of analytical tetracene standards **1** will also be added.
- [20] G. Manolikakes, M. A. Schade, C. M. Hernandez, H. Mayr, P. Knochel, *Org. Lett.* **2008**, *10*, 2765-2768.
- [21] S. D. McCann, S. S. Stahl *Acc. Chem. Res.* **2015**, *48*, 1756-1766 (overview); (b) J. M. Hoover, B. L. Ryland, S. S. Stahl, *J. Am. Chem. Soc.* **2013**, *135*, 2357-2367 (mechanism).
- [22] H. H. Tso, T. K. Hwang, Y. J. Chen, *Bull. Inst. Chem., Academia Sinica* **1994**, *41*, 25-32.
- [23] Z. Liang, W. Zhao, S. Wang, Q. Tang, S.-C. Lam Q. Miao, *Org. Lett.* **2008**, *10*, 2007-2010.
- [24] For use of pre-prepared and *in situ* use of BF₃-H₂O mixtures see: (a) G. K. S. Prakash, C. Panja, A. Shakhmin, E. Shah, T. Mathew, G. A. Olah, *J. Org. Chem.* **2009**, *74*, 8659-8668; (b) S. Zhang, X. Zhang, X. Ling, C. He, R. Huang, J. Pan, J. Lia, Y. Xiong, *RSC Adv.* **2014**, *4*, 30768-30774.
- [25] F. Mata-Perez, J. F. Perez-Benitol, *J. Chem. Edu.* **1987**, *64*, 925-927.
- [26] L. M. Geary, T.-Y. Chen, T. P. Montgomery, M. J. Krische, *J. Am. Chem. Soc.* **2014**, *136*, 5920-5922 [Tetracene **1aa** is widely and well characterised, ref. 26 gives: ¹H and ¹³C NMR spectra, an IR and HRMS].
- [27] E. A. Coulson, *J. Chem. Soc.* **1935**, 77-83 [Only an approximate m.p. and very poor analytical data have ever been reported for **1ab**].
- [28] W. von E. Doering, K. Sarma, *J. Am. Chem. Soc.* **1992**, *114*, 6037-6043 [The m.p., IR, ¹H and ¹³C NMR spectra of **1ac** are reported].
- [29] B. Hilti, C. W. Mayer, *US Patent* 4601853 A1 (to Ciba-Geigy Corporation), 1986, pp. 6 [*Chem. Abs.* **1986**, *104*, 100547; only UV-vis data and a low resolution MS are available].
- [30] The compound has been claimed as a starting material but no details of its preparation or properties are given: B. A. Hess, L. J. Schaad, W. C. Herndon, D. Biermann, W. Schmidt, *Tetrahedron* **1981**, *37*, 2983-2988.
- [31] E. A. Coulson, *J. Chem. Soc.* **1934**, 1406-1412 [Only an approximate m.p. and very poor analytical data have ever been reported for **1bb**].
- [32] J. Zhang, Z. Chen, L. Yang, F.-F. Pan, G.-A. Yu, J. Yin, S. H. Liu, *Nature Sci. Rep.* **2016**, *6*, 36310.
- [33] J.-L. Bredas, *Mater. Horiz.* **2014**, *1*, 17-19.

Graphical Abstract and Table of Contents text

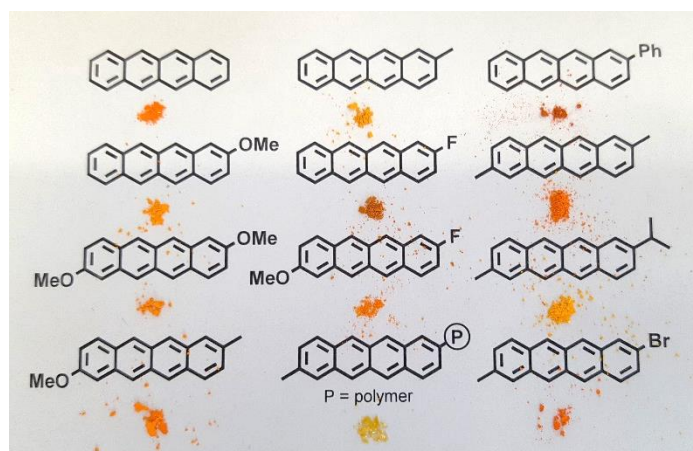

A simple procedure for the preparation of substituted tetracenes from low cost ArCH₂Cl and HOCH₂CCCH₂OH.

Keywords:

Arenes • Aldehydes • Aromaticity • C-C coupling • Acenes • Bradsher cyclisation • Efficient