

Mix Design Considerations of Foamed Bitumen Mixtures with Reclaimed Asphalt Pavement Material

Kranthi Kuna¹, Gordon Airey², Nick Thom³

(¹Pavement Engineer, Mott MacDonald, the United Kingdom, kranthi.kuna@mottmac.com)

(²Professor, University of Nottingham, the United Kingdom, gordon.airey@nottingham.ac.uk)

(³Lecturer, University of Nottingham, the United Kingdom, nicholas.thom@nottingham.ac.uk)

ABSTRACT

In the present work a mix design parametric study was carried out with the aim of proposing a practical and consistent mix design procedure for Foamed Bitumen Mixtures (FBMs). The mix design parameters that were adopted in the study are mixing and compaction water content (MWC), compaction effort using a gyratory compactor and aggregate temperature. This parametric study was initially carried out on FBMs with virgin limestone aggregate (VA) without Reclaimed Asphalt Pavement (RAP) material and a mix design procedure was proposed. This proposed methodology was also found to apply to FBMs with RAP. A detailed consideration was also given to characterising the RAP material so as to understand its contribution to the mechanical properties of FBMs.

Optimum MWC was achieved by optimising mechanical properties such as Indirect Tensile Stiffness Modulus (ITSM) and Indirect Tensile Strength (ITS-dry and ITS-wet). A rational range of 75-85% of Optimum Water Content (OWC) obtained by the modified Proctor test was found to be the optimum range of MWC that gives optimum mechanical properties for FBMs. It was also found that the presence of RAP influenced the design foamed bitumen content, which means that treating RAP as black rock in FBM mix design is not appropriate. To study the influence of bitumen and water during compaction, modified Proctor compaction and gyratory compaction were employed on mixes with varying amounts of water and bitumen. By this the work also evaluated the validity of the total fluid (water + bitumen) concept that is widely used in bitumen-emulsion treated mixes, and found it not to be applicable.

Keywords: Foamed bitumen treated mixes, mixing and compaction water content, reclaimed asphalt pavement, mechanical properties, volumetrics, water-bitumen interaction

CBM	Cold Bituminous Mixtures
ER	Expansion Ratio
FB	Foamed Bitumen
FBM	Foamed Bitumen Mixture
FWC	Foaming Water Content
HL	Half-Life
HMA	Hot Mix Asphalt
ITS	Indirect Tensile Strength
ITSM	Indirect Tensile Stiffness Modulus
MDD	Maximum Dry Density
MWC	Mixing Water Content
NAT	Nottingham Asphalt Tester
N _{design}	Design number of gyrations
OWC	Optimum Water Content
RAP	Reclaimed Asphalt Pavement
VA	Virgin Aggregate
VMA	Voids in Mineral Aggregates

1 INTRODUCTION

2 Unlike for HMA (Hot Mix Asphalt), there is no universally accepted mix design method for FBMs.
3 Most of the agencies [1, 2] which use FBMs have their own mix design procedures which are the
4 result of numerous efforts over decades [3-9]. In spite of all these efforts, foamed bitumen application
5 in cold recycling in the United Kingdom suffers from the lack of a standardised mix design procedure.
6 As a result, the mix design parameters such as foam characteristics, mixing, compaction, curing and
7 testing that are being adopted are far from being standardised. To overcome this, research had been
8 undertaken at the University of Nottingham by Sunarjono (2008) [10] to develop a mix design
9 procedure by identifying critical mix design parameters. The research by Sunarjono focussed on the
10 influence of the bitumen type, the foaming conditions, foam characteristics and mixer type on the
11 mechanical properties of FBM. The major outcomes of the work were recommendations for
12 producing an optimised FBM in terms of mixer type and usage, selection of binder type, bitumen
13 temperature, and foam characteristics. Therefore this present study focussed on other mix design
14 parameters such as foamed bitumen content, MWC, and compaction effort. Thus, the primary
15 objective of the present study is to propose a practical and consistent mix design procedure with
16 emphasis on the use of the gyratory compactor.

17 The amount of water during mixing and compaction is considered as one of the most important
18 parameters in FBM mix design [11, 12]. The MWC of FBM is defined as the water content in the
19 aggregate when the foamed bitumen is injected. This helps in dispersion of the mastic in the mix [3,
20 13]. However, too much water causes granular agglomerations which do not yield optimum dispersion
21 of the mastic in the mix [14, 15]. In view of this fact many studies have been focussed on the
22 optimisation of MWC. Lee (1981) [16] and Bissada (1987) [17] optimised MWC with reference to
23 Marshall stability and found that the optimum MWC is very much dependent on other mix design
24 variables such as the amount of fines and bitumen content. Sakr and Mank (1985) [18] related the
25 MWC to other mix design variables and recommended a relationship among them to obtain optimum
26 MWC. However, this work was performed on a foamed bitumen stabilised sand mixture which did
27 not have any coarser fractions of aggregate. Moreover, the work was based on optimising the density,
28 without considering any mechanical properties. The concept of optimum fluid content was later
29 borrowed from emulsion mix design in which the sum of the water and bitumen content should be
30 close to OWC [5, 19] obtained by the modified Proctor test. This concept considers the lubricating
31 action of the binder in addition to that of water. Thus the actual water content of the mix for optimum
32 compaction is reduced in equal measure to the amount of bitumen incorporated. However, the work of
33 Kim and Lee (2006) [8] and Xu et al., (2012) [12], who optimised MWC based on both density
34 criteria and fundamental tests (ITS and tri-axial tests) on FBM Marshall specimens, calls into question
35 the lubricating action of bitumen in the mix. Although the above discussed works are very
36 informative, they have their limitations and little attention has been paid to optimising MWC using
37 gyratory compaction. Therefore, the present work was aimed at obtaining a rational range of MWC
38 for mix design with the help of fundamental tests such as ITS (BS EN 12697-23:2003) and ITSM (DD
39 213: 1993) on FBM specimens.

40 Because of the presence of the water phase, the compaction mechanism of FBMs is very
41 different from that of HMA. Various laboratory compaction methods such as Marshall compaction [5,
42 8, 12, 13], vibratory compaction [3, 7, 20], gyratory compaction [13, 21-23] have been used in the
43 past. There are very well-established guidelines for Marshall compaction [2] and vibratory
44 compaction [24, 25]. However, there are no set guidelines for a gyratory compaction method for
45 FBMs in terms of compaction effort (number of gyrations, gyration angle and applied pressure). Past
46 studies have evaluated the feasibility of using laboratory gyratory compaction on FBM (Table 1). In
47 these studies efforts were made to obtain the design compaction effort in terms of compaction
48 pressure, gyration angle and number of gyrations. The compaction pressures recommended by
49 Australian guidelines (0.24MPa and 1.38MPa from Table 1) were taken forward in SHRP (Strategic
50 Highway Research Program) work on HMA, resulting in recommendations of 0.6MPa and 1.25°
51 angle of gyration. Jenkins et al., (2004) [22]'s tabulated conditions were based on a single water
52 content and a single foamed bitumen content. From preliminary trials it was found that the 30
53 gyrations recommended by Kim and Lee were too few to achieve modified Proctor densities. The
54 ideal compaction effort has to produce mix densities that are achieved in the field. Therefore,
55 modified Proctor density which is used worldwide to represent field compaction is used as a reference

1 in the present study. It was understood from the past studies [10] that the permanent deformation
 2 behaviour of FBMs is sensitive to the number of gyrations, which might be attributed to the
 3 arrangement of the aggregate skeleton. Hence efforts were made to propose a design number of
 4 gyrations (N_{design}) and it was decided to use the SHRP recommended compaction conditions which are
 5 600kPa compaction pressure and 1.25° angle of gyration. During the optimisation of MWC, the
 6 compactability of these mixtures during modified Proctor compaction and Gyrotory compaction was
 7 also studied.
 8

9 **Table 1 Gyrotory compaction effort on FBMs by different researchers**

Summary of gyrotory compaction effort on FBM by different researchers				
	Number of gyrations (N)	Compaction pressure (MPa)	Gyration angle (degrees)	Reference density
Brennan (1983) [13]	20	1.38	N/A	2.25kg/m ³
Maccarrone et al.1994 [21]	85	0.24	2	Field density
Jenkins et al. (2004) [22]	150	0.6	1.25	Modified proctor density
Kim and Lee (2006) [8]	30	0.6	1.25	Marshall density (75 blows)
Saleh (2006b) [23]	80	0.24	2	Australian guidelines for HMA

10 **2 MATERIALS**

11 Alongside the bitumen and virgin aggregate, particular attention was given to RAP
 12 characterization. This is important as RAP characteristics have considerable effect on the mix design
 13 of cold bitumen mixtures (CBM) because of the amount of variability associated with RAP in terms
 14 of source, production, storage and usage. However, it has to be noted that studies have found that
 15 RAP is less variable than virgin aggregate if its storage or stockpiling is well managed and that
 16 bituminous mixtures produced with high RAP content are actually less variable [26].

17 It is known that in mix design of HMA containing RAP, the aged bitumen in the RAP is often
 18 considered as an active component during the mixing and the bitumen in the new bituminous mixture
 19 is adjusted using blending charts. This approach is rational as the mixing of HMA is usually carried
 20 out at temperatures above 140°C where the aged bitumen in the RAP is less viscous. However, this is
 21 not the case in CBMs containing RAP, in which mixing and compaction is carried out at ambient
 22 temperatures which are much lower than the temperature required for softening the aged bitumen.
 23 Hence, each of the different agencies treat the RAP differently in their CBM mix design procedure.
 24 Some agencies factor the contribution of the aged bitumen present in RAP while others do not. This
 25 conflicting consideration is due to the unknown effect of the properties of aged bitumen in the RAP
 26 on the properties of the added fresh bitumen and on the amount of bitumen to be added. To address
 27 these issues research is ongoing under the initiative of the CR (Cold Recycling) task group (TG6) of
 28 RILEM (TC-237 SIB). Most of the tests that were performed on RAP were part of the inter laboratory
 29 round robin testing programme on RAP characterization as a part of TG6.

30 **2.1 Bitumen**

31 In HMA mix design, the expected traffic and the regional climate influence the selection of the
 32 bitumen type. However in FBM mix design, foamability (foaming potential) of the bitumen and the
 33 mixture compactability also need to be considered during selection of the bitumen. In the present
 34 study a 70/100 penetration grade bitumen (90dmm penetration at 25°C and softening point of 45°C)
 35 was used.
 36

1
2

3 **2.2 Virgin aggregates**

4 The virgin mineral aggregate used in this study was carboniferous limestone from Derbyshire,
5 UK. The aggregates were stored separately in stockpiles of size fractions of 20mm, 14mm, 10mm,
6 6mm, dust (0.063mm < dust > 6mm) and filler (<0.063mm). The stocks were batched to attain the
7 design gradation for each of the mixes. Particle size distribution was determined according to BS EN
8 933-1:1997. The design gradation adopted in the present study is as plotted in Figure 1.

9 **2.3 Reclaimed Asphalt Pavement**


10 The RAP material used in the present study was supplied from a UK asphalt contractor. The
11 RAP was from a single source and from a well-managed stockpile before being delivered to the
12 laboratory. The RAP aggregate material from the quarry was initially air dried at room temperature in
13 the laboratory at $20\pm 2^{\circ}\text{C}$ for 24 hours and then placed in a thermostatically controlled oven at a
14 temperature of 40°C for 24 hours and thereafter sieved into different sizes to improve the consistency
15 of the material and to reduce variability in the RAP. These separated fractions were stored in sealed
16 containers for further use.

17 The basic properties that are recommended to be measured on RAP for use in HMA mix design
18 are aggregate gradation before and after bitumen recovery, bitumen content, bulk specific gravity of
19 recovered aggregates and recovered binder properties. Obtaining these properties is particularly
20 important in the mix design of CBMs as they often contain high amounts of RAP. In addition to the
21 above mentioned tests, fragmentation and cohesion tests were recommended by the CR task group
22 (TG6). These two tests are discussed in the following sections.

23 **2.3.1 Analysis on RAP constituents**

24 To determine mass/volume parameters such as VMA (Voids in Mineral Aggregate), the
25 aggregate volume properties have to be known. When RAP materials are included in the mixtures,
26 the determination process becomes more complicated as it is necessary to calculate the bulk specific
27 gravity of each aggregate component (virgin and RAP aggregate). Measuring specific gravity of the
28 RAP aggregate requires extracting the aggregate, recovering the bitumen, sieving the RAP aggregate
29 into coarse and fine fractions, and determining the specific gravity of each fraction. Before bitumen
30 recovery, the initial gradation, which is a basic characteristic of RAP, was ascertained in accordance
31 with BS EN 933-48 2:2012. To evaluate constituents of the RAP, a composition analysis was
32 conducted in accordance with BS 598-102:2003. The aggregates from the RAP were extracted by
33 centrifuge using Dichloromethane (DCM) as recommended by the standard. After extracting bitumen
34 from the RAP, sieve analysis was carried out on the extracted aggregates. The gradation of the RAP
35 including that of the recovered aggregate is shown in Figure 1.

36 Once the binder was extracted and recovered from the RAP materials, its properties such as
37 penetration and softening point were determined. To determine the chemical composition of the
38 recovered bitumen BS 2000 Part 143:2004 was followed in which the asphaltene contents were
39 precipitated using heptane (C_7H_{16}). The results of asphaltene content and physical properties of
40 recovered bitumen are presented in Table 2.

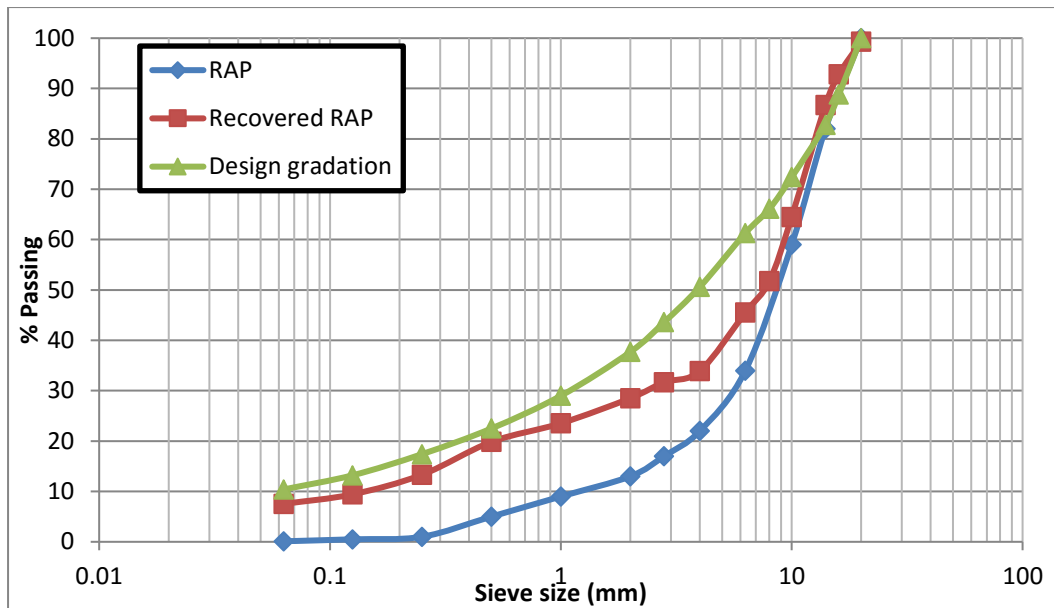

1
2 **Figure 1 Gradation of RAP and recovered aggregate**

3 **Table 2 Properties of recovered bitumen from 3 samples of RAP**


Recovered bitumen properties	RAP1	RAP2	RAP3	Average	Std. Dev.
Binder Content (%) (BS 598-102:2003, BS 598-101:2004)	4.5	4.7	4.4	4.5	0.1
Penetration (dmm) at 25°C (ASTM D5-05A)	20	16	17	17.7	1.7
Softening Point (°C) (ASTM D36-95(2000))	64.2	67.3	67.8	66.4	1.6
Viscosity at 135°C(mPa-s) (BS EN 13302:2003)	1077	1154	1189	1140	46.8
Asphaltene content (%) (BS 2000-143:2004)	35	N/A	N/A	N/A	N/A

4
5 **2.3.2 Homogeneity of RAP**

6 Verifying the homogeneity of RAP properties is an important step in quality control when
7 designing bituminous mixtures with RAP. This is particularly true in cold recycling in which high
8 amounts of RAP are often incorporated. Moreover, the mean values of the RAP properties are used to
9 adjust the required grading curve and to select the virgin bitumen. Therefore, homogeneity of RAP in
10 terms of gradation, bitumen content and the properties of recovered bitumen such as penetration,
11 softening point and viscosity was evaluated. Figure 2 shows the gradation of different samples of the
12 RAP before and after aggregate extraction. The figure also shows the standard deviation for each
13 particle size for both RAP and extracted aggregates. As can be seen from the figure the standard
14 deviations at all sieve sizes are reasonably low (maximum standard deviation is found to be 2.2%). It
15 should be noted that the extracted aggregates from the RAP were found to be less variable than the
16 RAP before bitumen recovery as seen in Figure 2.

17 Homogeneity of RAP was also evaluated with reference to the limits suggested by NCHRP
18 report 752 [27] and guidelines for the use of RAP in Lithuania [28]. The standard deviation of
19 recovered bitumen properties and extracted aggregate properties along with homogeneity limits
20 specified by the above mentioned references are presented in Table 3. As can be seen from the table
21 the standard deviations are well below the specified maximum limits which suggests the homogeneity
22 of the RAP used in the study was acceptable. It has to be noted that both the references suggest testing

1 of at least 10 samples. However in the present study only 3 samples were tested for homogeneity as
 2 recommended by RILEM TG6 technical committee.
 3

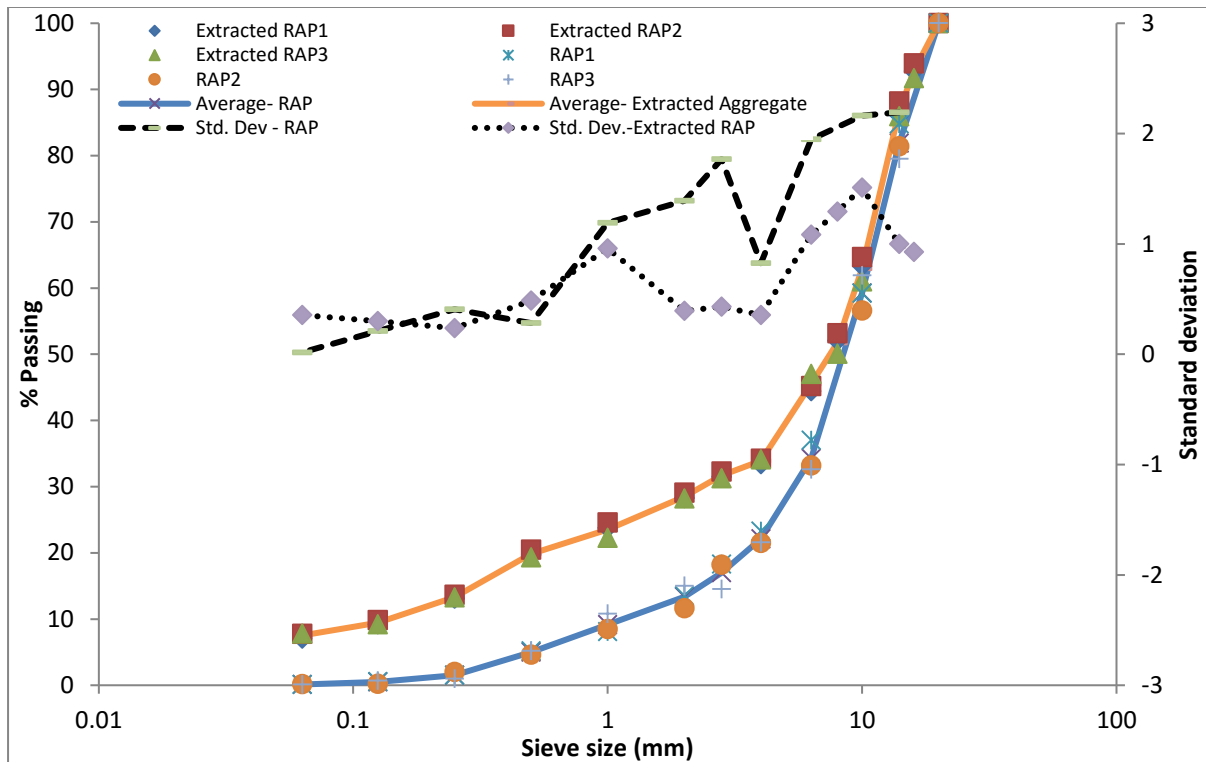

4
 5 **Figure 2 Homogeneity evaluation of RAP in terms of gradation**

6 **Table 3 Homogeneity limits for RAP stockpile**

Properties of RAP constituents after bitumen recovery	Standard Deviation	Allowable Standard deviation	Reference
Binder Content (%)	0.1	0.5	NCHRP-752[27]
Penetration (dmm) at 25°C	1.7	4	Lithuania[28]
Softening Point (°C)	1.6	2	Lithuania
Aggregate gradation-all sieves (max)	1.5	5	NCHRP-752
Aggregate gradation-0.063mm sieve	0.35	1.5	NCHRP-752


7

8 **2.3.3 Fragmentation test on RAP**

9 The fragmentation test is an impact test which involves a normalised mass falling from a height
 10 for a fixed number of times onto the surface of the RAP and thereafter evaluating the amount of
 11 material passing the 1.6mm sieve. The coefficient of fragmentation is the ratio of the weight of the
 12 material before impact and the weight of the material passing the 1.6mm sieve after impact. The
 13 available guidelines for this test are from *French standard P 18-574: Granulats – Essai de*
 14 *fragmentation dynamique*. The standard requires the test to be carried out at different temperatures on
 15 the different sizes of the aggregate. As RAP includes bitumen, different results are expected at
 16 different temperatures (temperature sensitive material). The standard recommends using a 14 kg mass,
 17 lifted mechanically and allowed to fall under gravity on to the top surface of a RAP sample placed in

1 a steel mould of 100mm diameter and 50mm height. The number of blows depends on the size of the
 2 RAP in the mould. A similar impact test is also recommended in BS EN 1097-2:2010, which requires
 3 material to be placed in a steel cylinder and subjected to ten impacts from a hammer of mass 50 kg
 4 freely falling from 400mm height. The amount of fragmentation caused is measured by sieving the
 5 tested material using five specified test sieves. However in the present case modified Proctor
 6 compaction (BS EN 13286-2: 2004) which is also an impact test was employed as recommended by
 7 RILEM TG6 technical committee.


8 The modified Proctor compaction involves 56 blows with a standard rammer on each of 5
 9 layers. The rammer and mould specification are as mentioned in BS EN 13286-2: 2004. The RAP was
 10 tested in different size fractions, 14mm/20mm, 10mm/14mm and 4.5mm/10mm and at different
 11 temperatures, 5°C, 20°C and 40°C. The test was performed after conditioning the material for 4 hours
 12 at the test temperature. The results of the tests are presented in Figure 3. As can be seen from the
 13 figure, the coefficient of fragmentation has not followed any trend, which indicates that the test results
 14 are not, as might have been expected, temperature dependent.

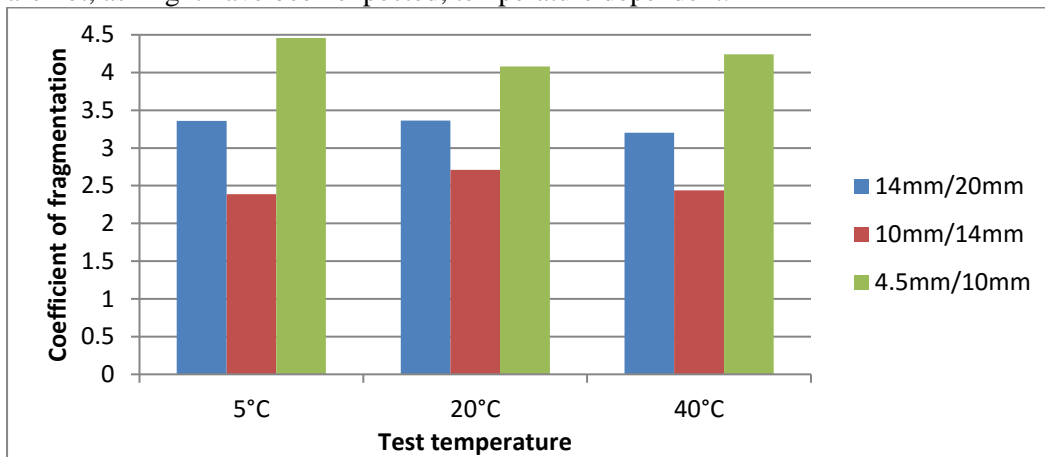

15
 16 **Figure 3 Fragmentation test results on RAP**

17 **2.3.4 Cohesion test on RAP**

18 Further to the above tests, to ascertain if the bitumen in the RAP could be classified as “active”
 19 or “inactive”, an indicative test was conducted, which is currently under investigation by the RILEM
 20 committee. This involved conditioning a sample of RAP for 4 hours at 70°C followed by the
 21 manufacture of three 100mm diameter by 63.5mm high specimens using Marshall compaction with
 22 50 blows per face. After compaction, Indirect Tensile Strength (ITS) tests in accordance with BS EN
 23 12697-23 were carried out at 20°C and then in wet conditions, soaked at 20°C for 24 hours. If the
 24 soaked ITS \leq 100kPa or the specimens do not hold together after compacting at 70°C, the RAP is
 25 considered to be inactive. For comparison, the test was also conducted with RAP conditioned at
 26 140°C. In all cases, the values exceeded 100kPa indicating that the binder in the RAP used in the
 27 study can be classified as active. The results are presented below in Figure 4.

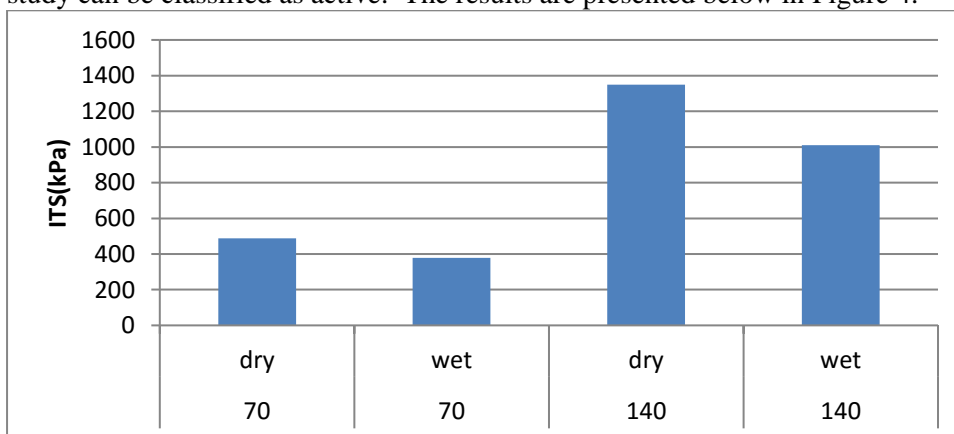

28
 29 **Figure 4 Cohesion test results on RAP**

3 METHODOLOGY

A detailed experimental design was prepared for the study and is tabulated in Table 4. The factors were selected by considering the findings of previous work done at the University of Nottingham [10] and Asphalt Academy (2009) [25]. The MWC was optimised on gyratory compacted specimens that were compacted to modified Proctor densities. The role of water and bitumen during gyratory and modified Proctor compaction can be analysed by a weight-volume relationship. In the present study, VMA, which is an indicator for compactability is used to understand the role of bitumen and water during compaction. VMA of a compacted specimen can be calculated using Eq. (1).


$$\text{VMA (\%)} = 100 - (\rho_b * P_s) / \rho_s \quad (1)$$

Where ρ_b is the bulk density of the specimen
 ρ_s is the bulk density of the aggregate (solids)
 P_s is aggregate content by weight of mix (%)


For Hot Mix Asphalt, HMA, Eq. (1) can be applied as it is, as it has only two components, aggregate and bitumen. The weight and volume constituents remain constant throughout and volumetric relationships such as bulk density remain independent of time of test. However, for FBMs in addition to aggregate and bitumen, water also exists in the mixture. But these FBMs lose water with time as can be seen in Figure 5. The figure represents change in constituents (solids, bitumen, water and air) per unit weight and unit volume over time (immediately after compaction (a), after a period of time (b) and in the dry state (c)). As can be seen in the figure neither weight nor volume constituents remain constant with time. This is because of the presence of the water phase in these mixtures. Hence, dry density (ρ_d) was used instead of bulk density (ρ_b) in Eq (1) to obtain VMA. Magnitude of constituents per unit of FBM with MWC of 85% of OWC and bitumen content of 4% can be seen in Table 5.

Table 4 Experimental design for mix design parametric study

Mix design parameter	factorial levels	Remarks
Bitumen type	90pen (70/100 grade)	constant throughout the experiment
Target Foam Characteristics	ER = 10	Asphalt Academy (2009) and Sunarjono (2008)
	HL (seconds) = 6	
Foaming conditions	Temperature (°C):170	constant throughout the experiment
	FWC (%): 3	
Mixer type	Pug mill type mixer	constant throughout the experiment
Aggregate type	limestone	constant throughout the experiment
Aggregate gradation	20mm (maximum size)	Asphalt Academy (2009), constant throughout the experiment
MWC	% of OWC: 65,75,85,95	variable to be optimised
foamed bitumen content	% of total weight: 2,3,4,5	variable to be optimised

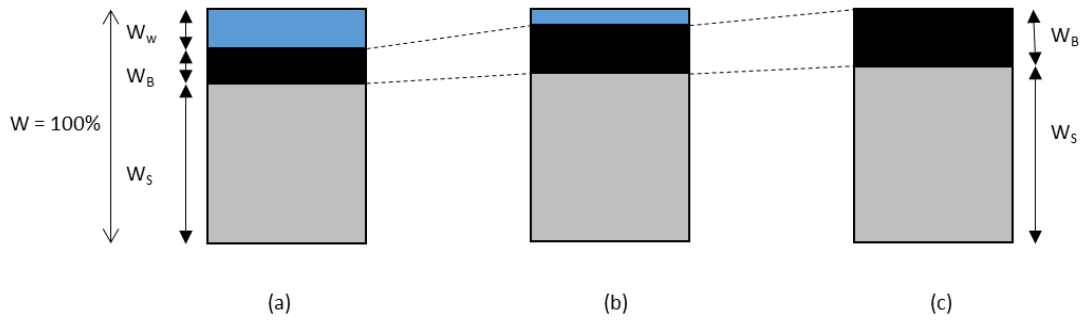

1. Constituents per unit weight in FBM

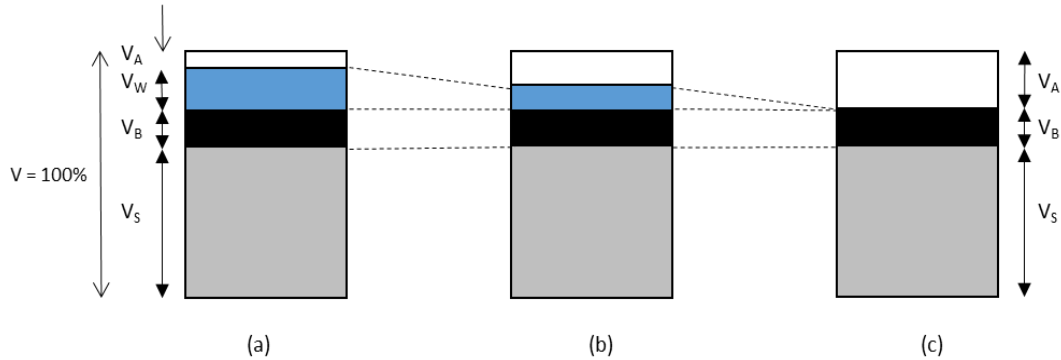

2. Constituents per unit volume in FBM

Figure 5 Change in weight and volume constituents per unit of FBM

Note: Figure is not to the scale

Table 2 Weight and volume constituents per unit of FBM

Constituents per unit of FBM with MWC of 85% of OWC and bitumen content of 4%						
	(a) Immediately after compaction		(b) 48 hours at 20°C after compaction*		(c) dry state	
	Weight (%)	Volume (%)	Weight (%)	Volume (%)	Weight (%)	Volume (%)
Air	0	4.4	0	10.4	0	15.7
Water	5.5	11.3	2.5	5.3	0	0
Bitumen	4	8.2	4.1	8.2	4.2	8.2
Solids	90.5	76.1	93.4	76.1	95.8	76.1

* First 24 hours in gyratory mould at 20°C

3.1 Mixing


Foamed Bitumen begins to collapse rapidly once it comes into contact with relatively cold aggregates. Therefore, the mixing process should be a dynamic one. Consequently foamed bitumen is

1 most often applied directly from the laboratory foaming plant to the aggregate as it is being agitated in
2 the mixer. As different mixers can produce up to a 25% difference in strength [25] selection of an
3 appropriate mixer is very important in the production of FB mix. It is always recommended to utilise
4 a mixer that simulates site mixing. Pug mill drum mixers and milling-drum mixers are the most
5 commonly used mixers on site for the production of FBM. These mixers provide sufficient volumes in
6 the mixing chamber and energy of agitation to ensure better mixing [3]. A pug mill type mixer is
7 therefore recommended for production of FBM representative of the field [29]. Hence, a twin shaft
8 pug mill mixer was adopted in this work (operated at $20\pm 2^{\circ}\text{C}$). Mixing time should be in accordance
9 with the time required by the bitumen foam to collapse. In the laboratory a mixing time of 60 seconds
10 has been recommended [17] which is longer than in situ mixing but simulates the difference in the
11 energy of the laboratory mixer and field plant and the same (60 seconds mixing time) was adopted in
12 this study.

13
14 The optimisation of MWC was carried out on specimens compacted using the gyratory
15 compactor to densities that were obtained by modified Proctor compaction. Targeting modified
16 Proctor densities meant that all specimens were compacted to the same compaction effort. This
17 approach was considered suitable as it is not appropriate to compact mixtures with different water
18 contents to the same density as they would need very different compaction efforts. For example,
19 mixtures with 100% of OWC (6.5% by weight of mixture) needed 200 gyrations to compact to MDD
20 while a mixture with 65% of OWC (4.25% by weight of mixture) required around 340 gyrations.
21 Hence, modified Proctor compaction was carried out on aggregate and water mixtures in accordance
22 with BS EN 13286-2: 2004. The results of the modified Proctor compaction can be seen Figure 6,
23 including results of modified Proctor compaction on mixtures with RAP. As can be seen from Figure
24 6, the OWC for 100% VA mixtures was found to be 6.5% and for mixtures with RAP the OWC was
25 around 6%.


26 Once OWC from modified Proctor compaction had been obtained, mixing was carried out with
27 varying water content (65%, 75%, 85% and 95% of OWC, which corresponds to 4.2%, 4.9%, 5.5%
28 and 6.2% water content in the mixture) and varying FB content (2%, 3%, 4%, and 5%). These
29 mixtures were compacted using modified Proctor compaction; densities were obtained and the results
30 for 100% VA are presented in Figure 7. After obtaining the densities, these possible combinations of
31 mixtures were mixed and compacted using a gyratory compactor (angle of gyration 1.25° and
32 compaction pressure 600kPa) using different numbers of gyrations to obtain the achieved modified
33 Proctor densities. Gyratory compacted moulds after compaction were kept at room temperature for 24
34 hours and then the specimens were extracted. The extracted specimens were cured at 40°C and the
35 water content of the specimen was monitored over time. Mechanical tests were carried out (at ambient
36 room temperatures of $20\pm 2^{\circ}\text{C}$) on the cured specimens after 3 to 5 days depending on the amount of
37 water in the specimen. The tests were carried out on all specimens at approximately the same water
38 content (between 0.6% and 0.65%) to eliminate the effect of water content on the measured
39 mechanical properties. The effect of mixing water content on the mechanical properties can be seen in
40 the plots in Figure 8.

41 The mechanical properties (ITSM, ITS-dry and ITS-wet) of gyratory-compacted and cured
42 specimens are plotted against MWC in terms of % of OWC in Figure 8. Each ITSM value in the plot
43 is an average of tests on 8 specimens and ITS-dry and ITS-wet are averages of 4 specimens. The
44 properties were all measured at the same water content (0.6-0.65%). As can be seen from the figures,
45 the approximate peak ITSM values were 85% of OWC, except for 2%FBM (FBM with 2% FB
46 content). When ITS-dry results were considered, the optimum MWC was seen at 85% of OWC for
47 2%FBM and 3%FBM; and for 4% FBM and 5% FBM the peak was at 75%. For ITS-wet values the
48 optimum was found at 85% except for 5% FBM. Overall, the optimum MWC for all mixtures was
49 consistently found to lie between 75% and 85% of OWC.

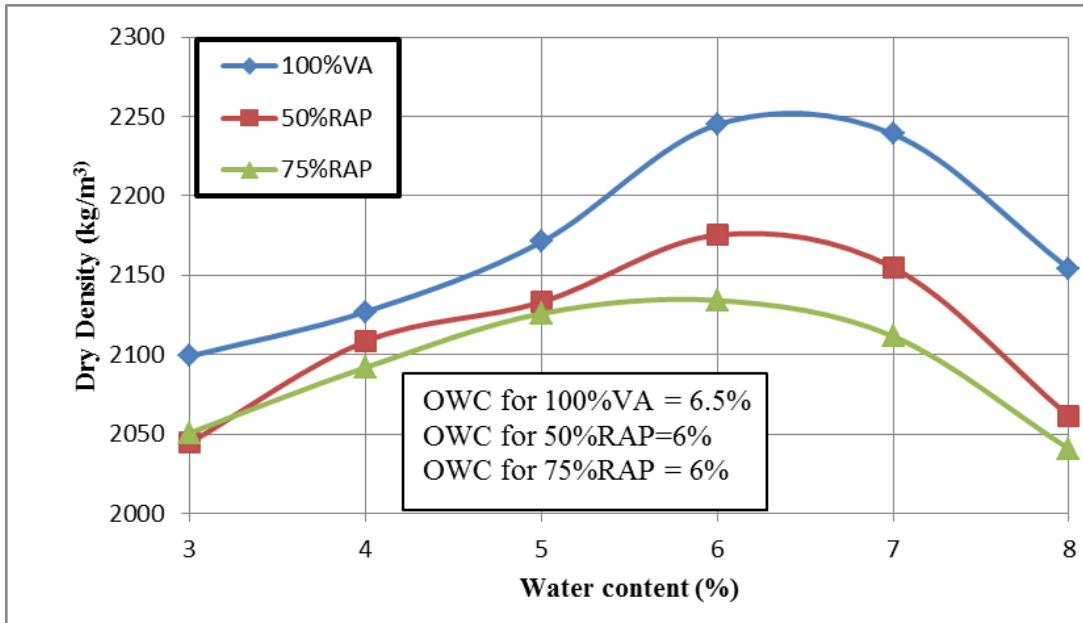

1
2

Figure 6 Modified Proctor test results on aggregate and water (only) mixtures

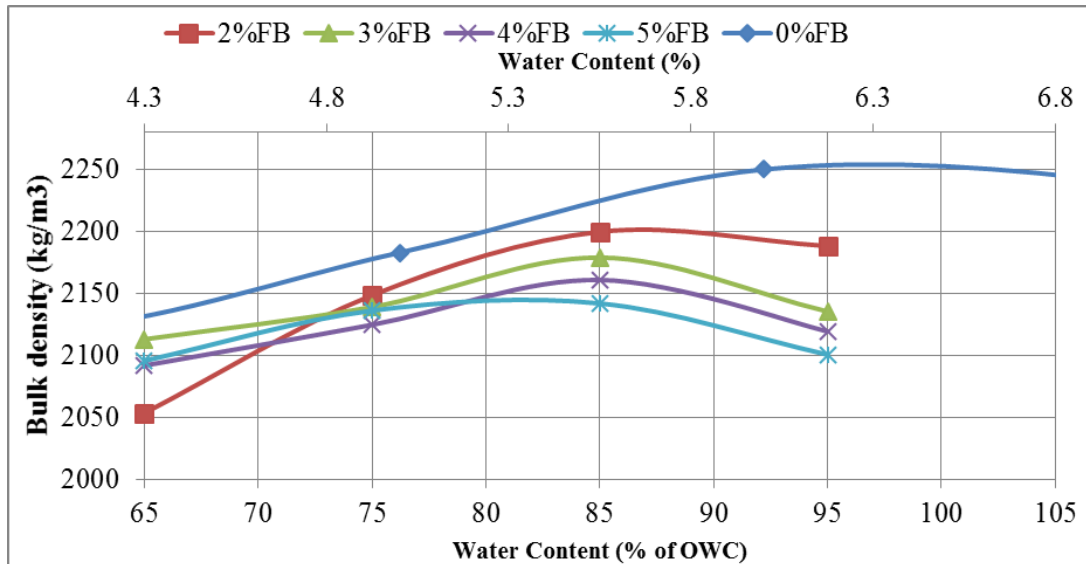


3

4

5


Figure 7 Modified Proctor compaction results on 100%VA-FBM with varying FB and water content

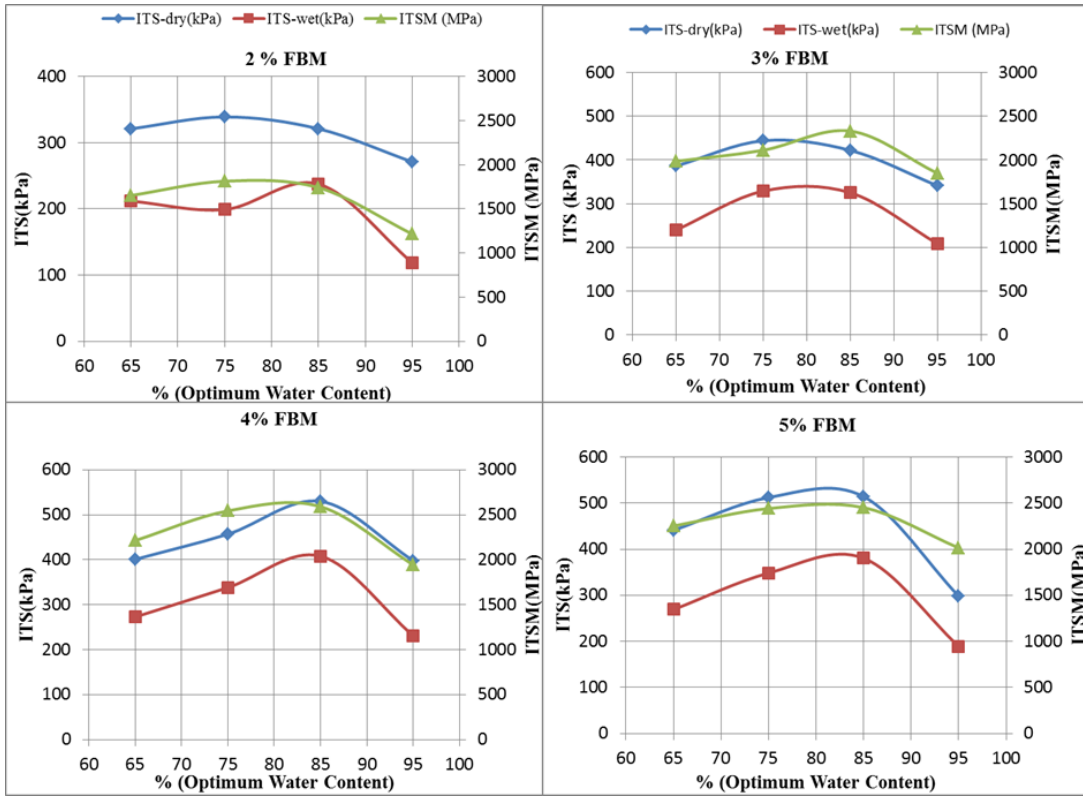

1
2 **Figure 8 Mechanical properties of 100%VA- FBM with varying FB and water content**

3 **3.1.1 Compaction effort**

4 As discussed in the earlier sections, one of the objectives of this study was to propose a
5 design number of gyrations (N_{design}) for FBM mix design. For this, aggregate mixtures with 80% of
6 OWC (based on the 75% to 85% range established above) and different FB contents were prepared.
7 Then the mixtures were compacted to 200 gyrations and densities were plotted against number of
8 gyrations as shown in Figure 9. From the data, the number of gyrations required to reach modified
9 Proctor density was identified as can be seen in Figure 9. To study the optimum compaction effort
10 and to obtain the design number of gyrations (N_{design}), the changing height was recorded from the gyratory
11 compactor during compaction. From the height data, density was calculated and plotted against
12 number of gyrations (Figure 9). The marks on the curves are the target densities that were obtained
13 from modified Proctor data. It can be seen from the plots that, though the target densities were
14 different, the number of gyrations required to compact to those target densities are in a similar range.
15 That means, a design number of gyrations required to compact to modified Proctor density can be
16 established, independent of foamed bitumen content in the mixture. N_{design} for all FBMs considered
17 was in the range of 120-160 gyrations; 140 gyrations has therefore been selected as giving an
18 equivalence to modified Proctor.
19
20

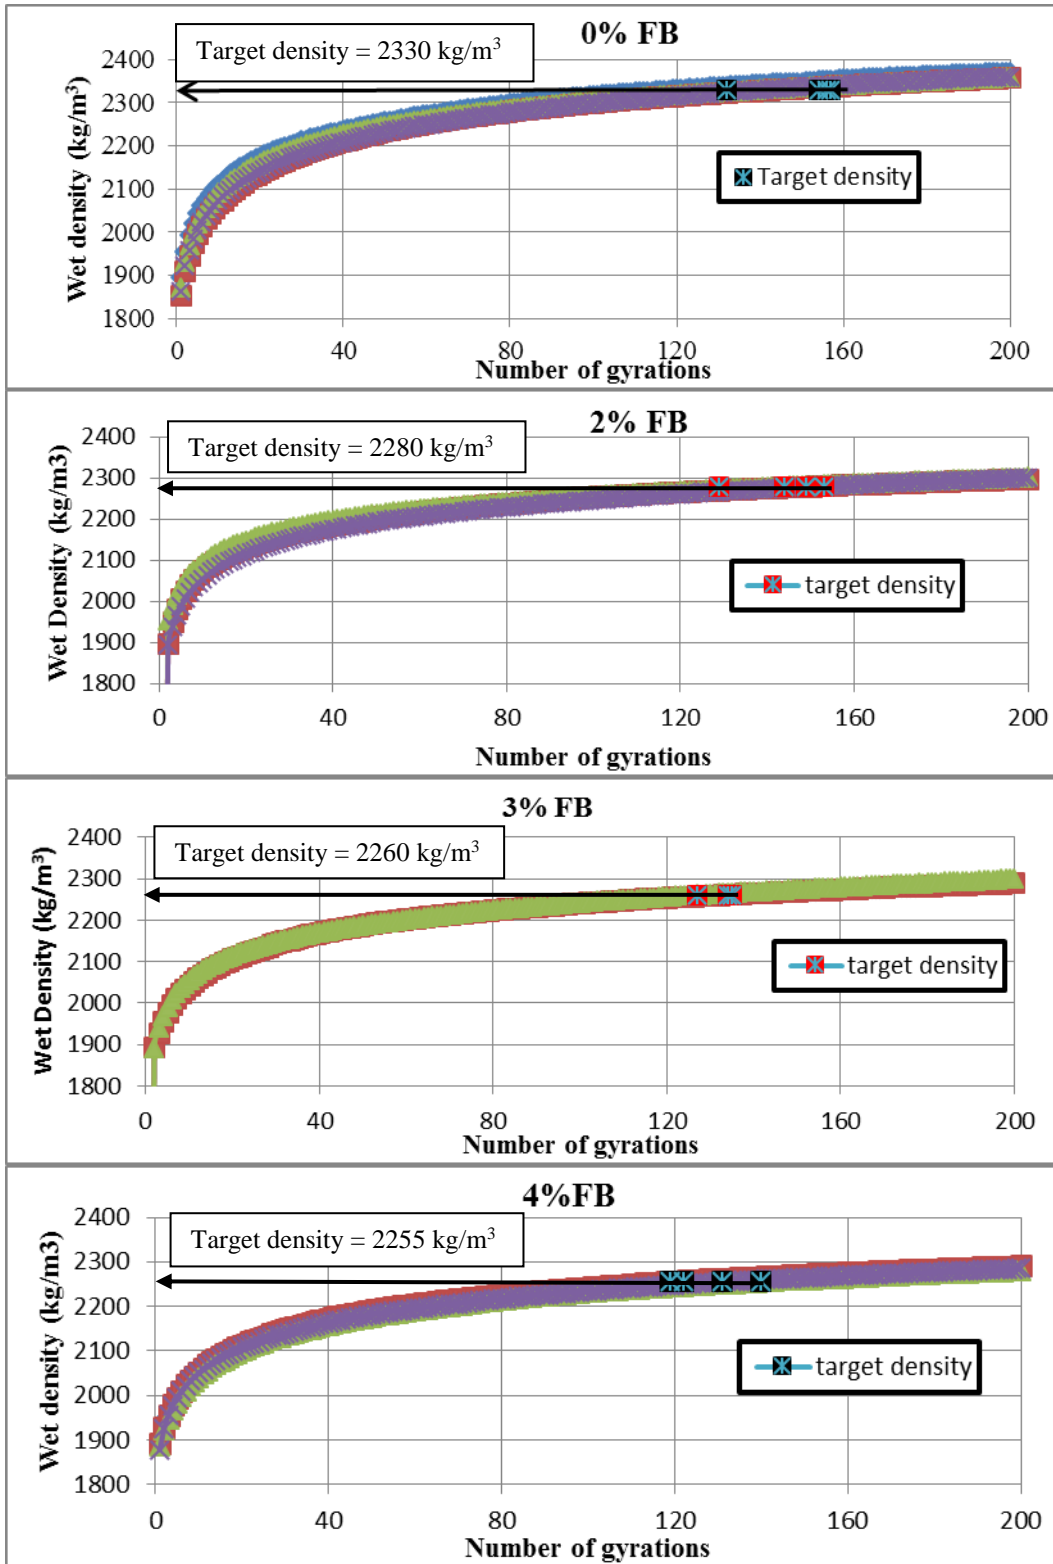

1

2

3

4

5

6

7

8

9

10

11

Figure 9 Obtaining design number of gyrations for FBM (Mixing water content of the mixture (MWC) = 80 % (OWC) = 5.2%)


3.1.2 Compactability of FBMs

The compactability of FBMs was studied on mixtures with varying amounts of bitumen and water. As discussed previously, the modified Proctor compaction and Gyratory compaction methods were considered. The study enables the role of bitumen and water with these compaction methods to be understood. As seen in Figure 10, from tests on modified Proctor compacted specimens, all curves

1 give optimum water content. However, that optimum differs only slightly from one bitumen content
 2 to another, implying that the bitumen hardly contributes to the ‘fluid’ needed for compaction. The
 3 same effect can be seen in terms of volumetrics in Figure 11, where VMA is plotted against total fluid
 4 (water + bitumen). The optimum shifts to the right in steps and the shift is around 1% for the 2%, 3%,
 5 4%, 5% FB curves, again implying negligible contribution from the bitumen.


6 A similar picture is obtained from the volumetrics of gyratory compacted specimens. To study
 7 the gyratory compaction, the FBMs were compacted to 140 gyrations with an angle of gyration of
 8 1.25°, compaction pressure of 600kPa and 30 revolutions per minute. The compactability was studied
 9 using weight-volume relationships and voids in aggregate (VMA) as calculated by Eq.1. VMA at 140
 10 gyrations for mixtures with different bitumen content is plotted against MWC (dashed lines) in Figure
 11 10 (each point is an average of five data points), alongside the data from modified Proctor compaction
 12 (solid lines). As can be seen from the figure, the VMA of the specimens at optimum was almost the
 13 same in the two cases, very slightly greater for modified Proctor compaction, and it increased as the
 14 foamed bitumen content increased. The optimum water content was also typically slightly higher in
 15 the case of gyratory compaction, thought to be due to the significant difference in the way the two
 16 compaction processes operate.

17 Overall however, the clear implication is that the bitumen gives minimal contribution during
 18 compaction and that this phenomenon is observed for both the compaction methods that were
 19 considered. Thus, the total fluid content, which has been successfully used in bitumen emulsion mix
 20 design [30-32], is not a valid parameter in FBM mix design.

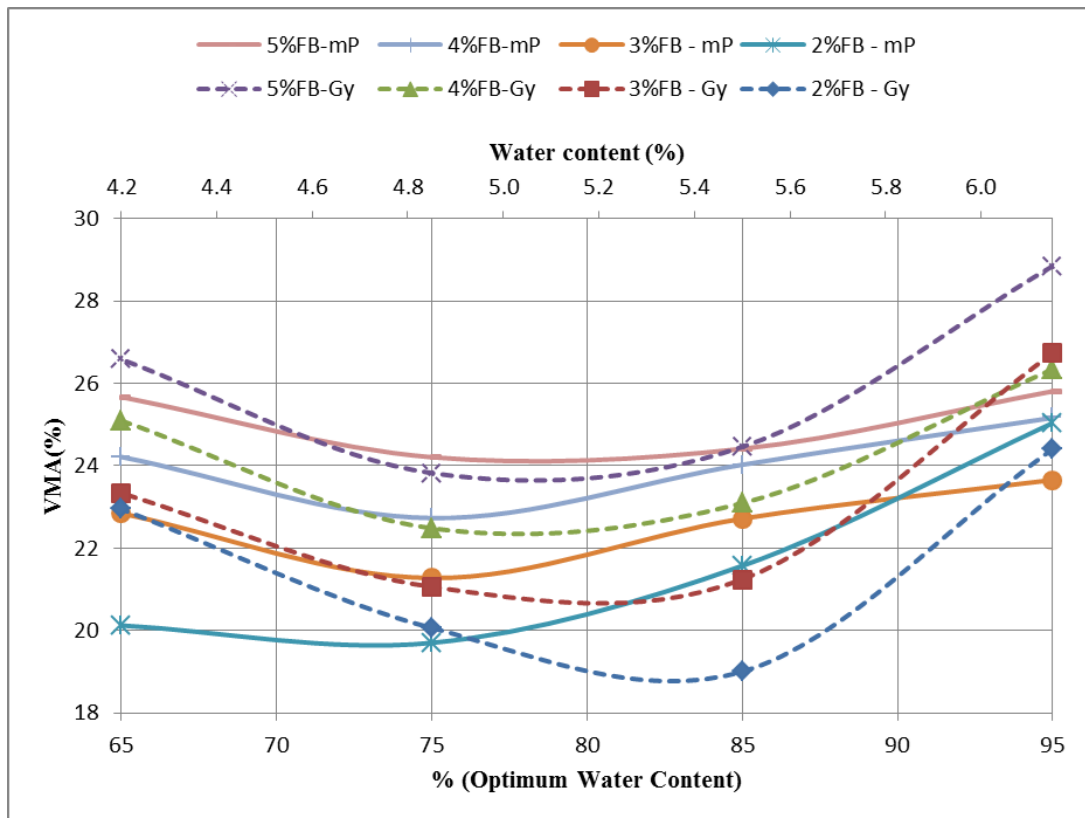

22 **Figure 10 Role of bitumen and water during gyratory (Gy) and modified Proctor (mP)**
 23 **compaction**
 24

25

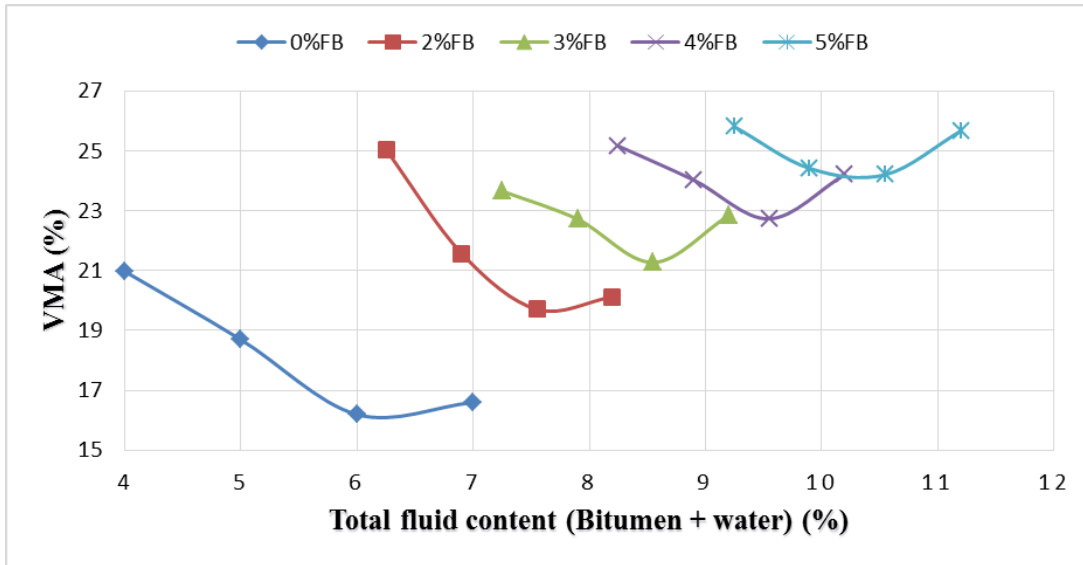


1
2 **Figure 11 Role of bitumen and water during modified Proctor compaction**


3 **3.2 Mechanical properties of FBMs with RAP**

4 The mix design parametric study discussed in the previous sections was done on mixtures with
5 VA (100%VA-FBM). In this section, a study has been conducted on mixtures with RAP (50%RAP-
6 FBM and 75%RAP-FBM) to validate the proposed recommendations. To validate the MWC range
7 proposed (75% - 85% of OWC), aggregates with 50%RAP and 75%RAP and 4% FB were mixed and
8 compacted with varying MWC (95%, 85%, 75% and 65% of OWC) to modified Proctor densities of
9 similar mixtures. 4% FB was selected as it was the design FB content obtained for 100%VA mixes
10 and it was assumed that the presence of RAP would not affect the design FB content (an assumption
11 that was later shown to be incorrect). The specimens were cured as discussed for 100%VA-FBMs.
12 The results of mechanical tests carried out on cured specimens are presented in Figure 12. These tests
13 were performed at ambient room temperature of 20±2°C. ITSM values shown in figure are the
14 average of 10 tests while ITS-dry and ITS-wet are the average of 5 tests each. As can be seen from the
15 figure, the optima for ITSM and ITS-dry were found at 75% of OWC and 85% of OWC respectively.
16 For 75%RAP-FBM, optimum ITS-dry and ITS-wet were found at 75% of OWC. Although ITS-wet
17 for 50%RAP-FBM and ITSM for 75%RAP-FBM didn't showed any clear optimum, other properties
18 of both the mixtures have their optimum in the proposed range (75% - 85% of OWC).

19 To validate the N_{design} , the aggregates with RAP were mixed and compacted with 0%, 3%, 4%
20 of foamed bitumen and the density data is plotted in Figure 13. For clarity the figure shows only data
21 for 75%RAP-FBM with 0% and 3% of foamed bitumen; the data for 4% foamed bitumen lies in the
22 same region on plot. It can be seen that the N_{design} range is the same, i.e. between 80 and 120
23 gyrations. The mid-point of this range which is 100 was considered as N_{design} . The study conducted on
24 50%RAP-FBM gave N_{design} as 110 gyrations.
25

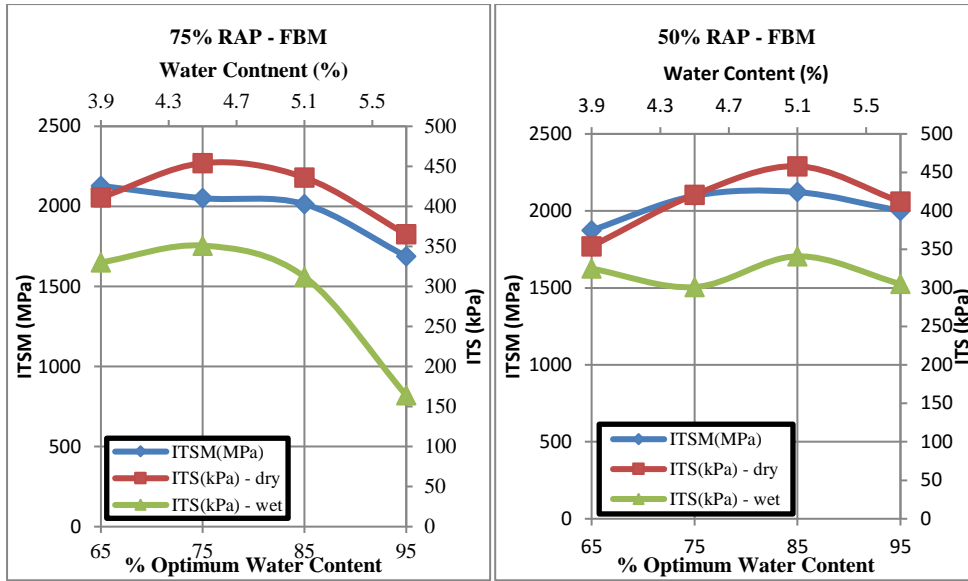

1
2 **Figure 12 Mechanical properties on 50%RAP-FBM and 75%RAP-FBM with 4% FB content**
3 **(Validation)**

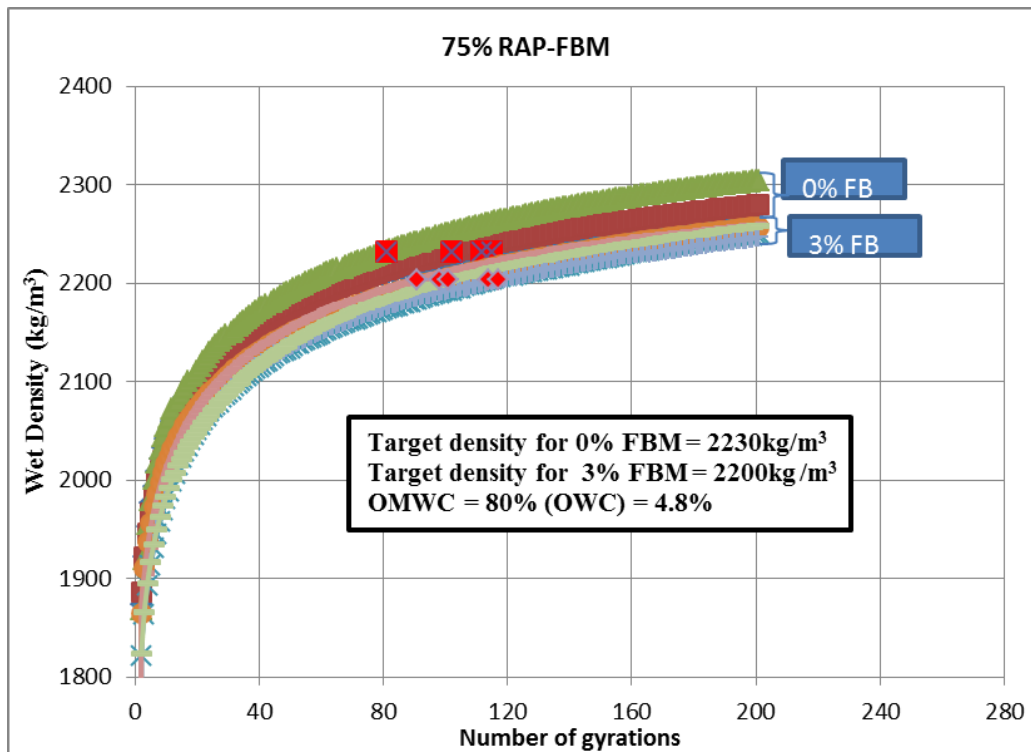


4
5 **Figure 13 Validation of N_{design} for 75%RAP-FBM**

6 **3.3 Foamed Bitumen (FB) content optimisation**

7 The results of mechanical tests on the mixtures that were compacted at optimum MWC (80% of
8 OWC) and to N_{design} , and varying FB content, are plotted in Figure 14. As can be seen in the plots
9 there is a clear optimum ITSM value for all mixtures. For 100% VA mixtures, the optimum was found
10 at 4% FB content. Similarly, the optimum ITSM values for 50%RAP and 75%RAP mixtures were
11 found at 3.5% and 3% FB content respectively. If ITS-dry values are considered, there was no
12 optimum for 100%VA mixtures. ITS-dry values for these mixtures increase with increasing FB
13 content without any optimum value. However, an optimum could be located for both the mixtures
14 with RAP (50% RAP and 75% RAP). The optimum values were found at 3.5% and 3% FB

1 respectively. When ITS-wet results are considered, the optimum ITS-wet was found only for 75%
 2 RAP mixtures, which is at 3% FB content. There was no optimum for any mixtures if ITSR (Indirect
 3 Tensile Strength Ratio) was considered. However, it can be noted that, though the maximum ITSM
 4 value was higher for 100%VA than for mixtures with RAP, most maximum ITS and ITSR values
 5 were found to be superior for mixtures with RAP. This indicates that the mixtures with RAP have
 6 better resistance against water than mixtures without any RAP. This could be attributed to the
 7 presence of fully bitumen coated RAP aggregates in the mixture. Overall, it was clear that at 4% and
 8 3% foamed bitumen contents, optimum mechanical properties were found for 100%VA and 75%RAP
 9 mixtures respectively. However, optimum foamed bitumen content was less clear for 50%RAP
 10 mixtures.

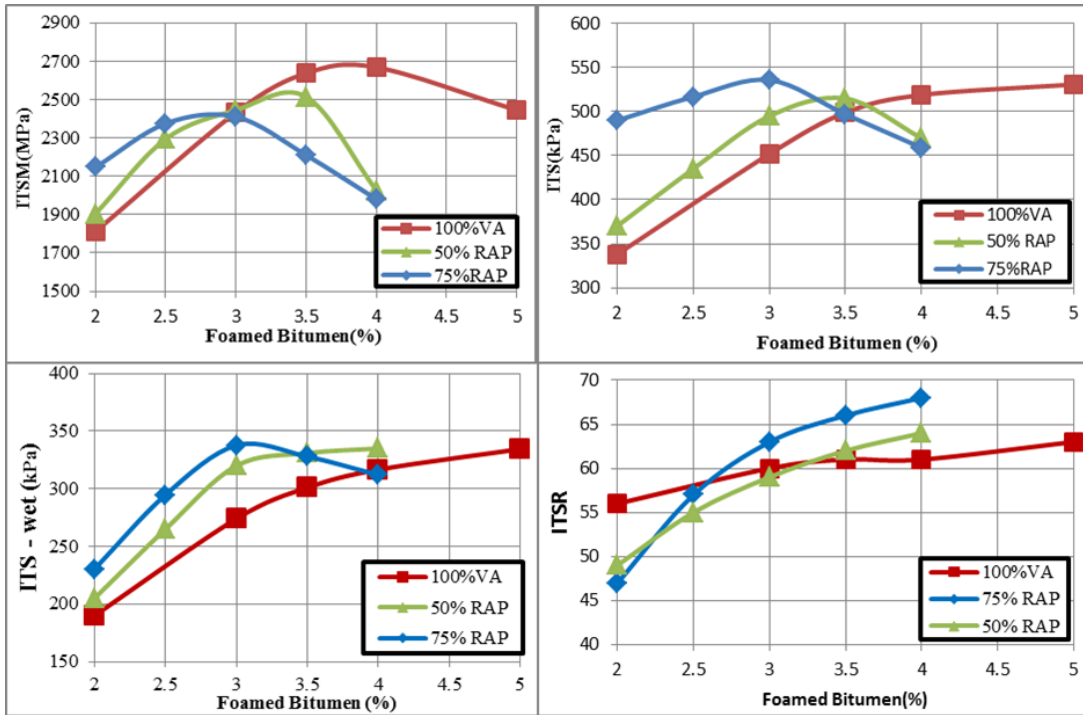

11
 12 **Figure 14 Mechanical properties of FBMs that were mixed at optimum MWC (80% of OWC)**
 13 **and compacted to N_{design}**

14 **3.4 Effect of aggregate temperature on mechanical properties**

15 Temperature of the aggregate during the mixing phase influences significantly the quality of
 16 FBM [33]. Because of this reason it has been recommended to construct pavements with FBM only if
 17 the ambient temperature is above 10°C [24, 25]. As was mentioned previously, the present
 18 experimental study mostly involved mixing and compaction at an ambient temperature of 20±2°C.
 19 However, this section has analysed the effect of aggregate temperature (which is also mixing
 20 temperature in the field) on the mechanical properties of FBM with 50 % RAP aggregate (50% RAP-
 21 FBM). The mixing was carried out at three aggregate temperatures (5°C, 20°C and 30°C). Before
 22 mixing, the aggregates were conditioned at the required temperature overnight (around 18 hours). The
 23 resulting temperatures of the mixtures after foaming and mixing were found to be 10°C, 26°C and
 24 31°C respectively for aggregate temperatures of 5°C, 20°C and 30°C. The mixtures were then
 25 compacted at an ambient room temperature of 20±2°C. The mechanical tests were carried out on
 26 samples that were extracted after 24 hours and cured at 40°C for 72 hours (3 days). The results of the
 27 mechanical tests and volumetric properties of the cured specimens can be seen in Figures 15 to 16.

28 As can be seen in Figure 15 aggregate temperature has significance influence on compaction
 29 (air voids) and stiffness (ITSM) of the FBM. The lower aggregate temperatures resulted in inferior
 30 mixture properties. Though the difference is not significant from 20°C to 30°C, the aggregate
 31 temperature of 5°C clearly resulted in higher air voids and less stiff mixtures. Similar results were
 32 also found when comparison was made in terms of strength (ITS-dry and ITS-wet) (Figure 16).

Moreover the retained strengths (ITSR) increased with increase in aggregate temperature, which reinforces the finding of poor mixing and compaction at lower aggregate temperature.

The major determinate for poor mixing at low aggregate temperature is the high temperature gradient between the aggregate and the foamed bitumen which influences the rate of collapse of the foam. A high temperature gradient causes rapid collapse of the foam as the film of the bitumen bubbles is thin, which allows rapid heat transfer between foamed bitumen and aggregate. Consequently, less time is available for foamed bitumen to interact with the aggregate resulting in poor coating of the aggregate particles and inconsistent dispersion of the mastic in the mixture. As can be seen in Figure 15 the high temperature aggregates resulted in lower air voids in the resulting specimens. These higher densities (low air voids) could be associated with better compactability of the mixture at higher temperatures. As discussed the higher aggregate temperatures resulted in mixtures with relatively higher temperatures which helps in obtaining denser specimens [3, 14]. However, it has to be noted that the difference in densities between aggregate temperatures of 20°C and 30°C was found to be marginal.

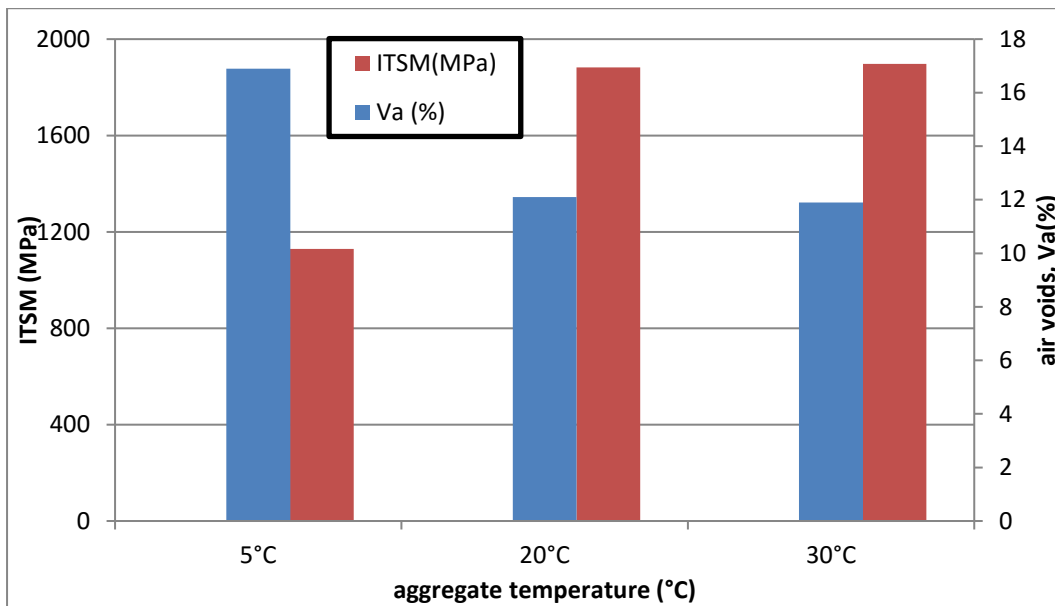


Figure 15 Effect of aggregate temperature on air voids and stiffness in 50%RAP - FBM

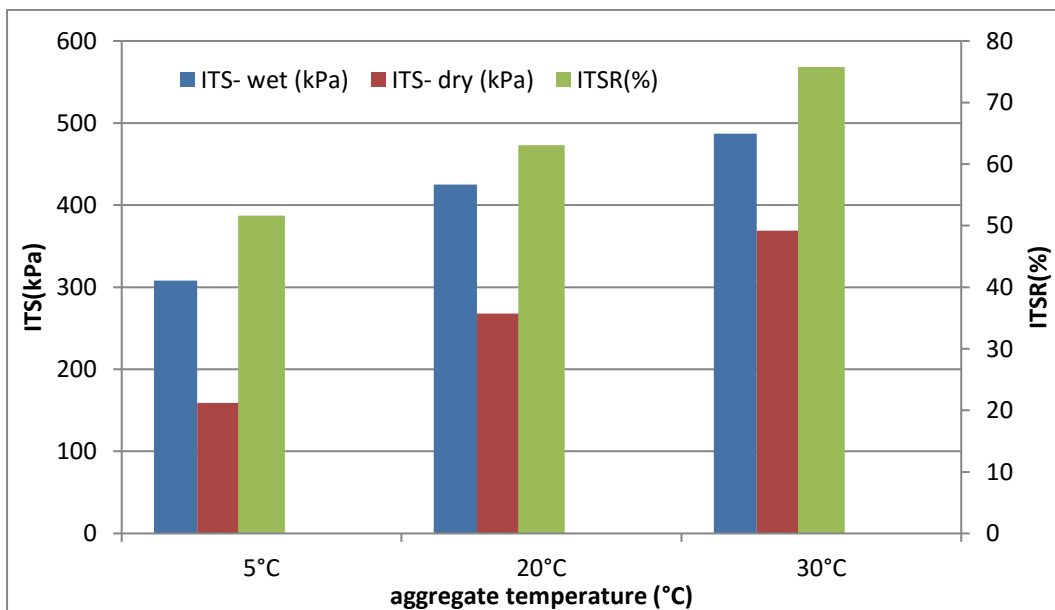


Figure 16 Effect of aggregate temperature on strength in 50%RAP - FBM

4 CONCLUSIONS

This paper has focussed on the development of a practical and consistent mix design procedure for FBM with the main focus being on the use of the gyratory compaction method in the proposed methodology. The study also evaluated the effect of the aggregate temperature on the mechanical properties of the FBMs. To attain this objective, the mix design parameters such as MWC and compaction effort have been optimised. This mix design parametric study was initially carried out on FBMs with virgin limestone aggregate without RAP material and a mix design procedure was proposed. The proposed methodology was later validated on FBMs with RAP. In the present study particular attention has been given to RAP characterization. The tests on recovered aggregate and bitumen revealed that the RAP was well within the homogeneity limits recommended by different agencies. A cohesion test revealed that the RAP used in this study can be classified as active.

A rational range of 75-85% of OWC obtained by the modified Proctor test was found to be the optimum range of MWC that gives optimum mechanical properties for FBMs. As this study focussed on the use of the gyratory compactor for FBM compaction, efforts were made to suggest a design number of gyrations (N_{design}) for optimum compaction of FBMs. It was found that a unique N_{design} (mixture specific) which is independent of the foamed bitumen content can be established. N_{design} for the virgin mixture was found to be 140, while N_{design} for the mixtures with 50% of RAP and 75% of RAP was 110 and 100 respectively. It was also found that the presence of RAP influenced the design foamed bitumen content, which means that treating RAP as black rock in FBM mix design is not appropriate.

This work also evaluated the validity of the total fluid (water + bitumen) concept which is widely used in bitumen-emulsion treated mixes. It was observed that the bitumen gives minimal contribution during compaction and that this phenomenon was observed for both the compaction methods that were considered. Thus, the total fluid content, which has been successfully used in bitumen emulsion mix design is not a valid parameter in FBM mix design.

5 REFERENCES

1. Asphalt Academy., *Bitumen Stabilised Materials: A Guideline for the Design and Construction of Bitumen Emulsion and Foamed Bitumen Stabilised Materials*, 2009.
2. Wirtgen, *Cold Recycling Manual*, 2004.
3. Jenkins, K.J., *Mix Design Considerations for Cold and Half-warm Bituminous Mixes with Emphasis on Foamed Bitumen*, University of Stellenbosch, South Africa, 2000.
4. Ebels, L.J. and K.J. Jenkins. *Mix design of bitumen stabilised material: best practices and considerations for classification*. in *9th conference of Asphalt Pavements for South Africa*, 2007.
5. Muthen, K.M., *Foamed Asphalt Mixes: Mix Design Procedure*, CSIR TRANSPORTEK, 1998.
6. Acott, S.M. *Sand stabilization using foamed bitumen*. in *3rd Conf. on Asphalt Pavements for South Africa*, Durban, 1979.
7. Bowering, R.H. and C.L. Martin. *Foamed Bitumen Production and Application of Mixtures Evaluation and Performance of Pavements*. in *Association of Asphalt Paving Technologists*, 1976.
8. Kim, Y. and H. Lee, *Development of mix design procedure for cold in-place recycling with foamed asphalt*. *Journal of Materials in Civil Engineering*, Vol. **18**(1): p. 116-124, 2006.
9. Ramanujam, J.M. and J.D. Jones, *Characterization of foamed-bitumen stabilization*. *International Journal of Pavement Engineering*, Vol. **8**: p. 111-122, 2007.
10. Sunarjono, S., *The Influence Foamed Bitumen Characteristics on Cold Mix Asphalt Properties*, University of Nottingham, 2008.
11. Bowering, R.H., *Soil Stabilisation with Foamed Bitumen*. *Highway Engineering in Australia*, 1971.
12. Xu, J.Z., et al., *Study on the optimization design of mixing moisture content in foamed asphalt mix*. *Materials and Structures*, Vol. **45**(7): p. 1071-1085, 2012.

- 1 13. Brennan, M., *A Laboratory Investigation on the Use of Foamed Asphalt for Recycled*
2 *Pavement, Joint Transportation Research Program Technical Report*, Purdue University,
3 1983.
- 4 14. Ruckel, P.J., S.M. Acott, and R.H. Bowering, *Foamed - asphalt paving mixture: Preperation*
5 *of Design mixes and treatment of test specimens*. Transportation Research Board, Vol. 911: p.
6 88-95, 1982.
- 7 15. Fu, P., et al., *Investigation of the Curing Mechanism of Foamed Asphalt Mixes Based on*
8 *Micromechanics Principles*. Journal of Materials in Civil Engineering, Vol. **22**(1): p. 29-38,
9 2010.
- 10 16. Lee, D.Y. *Treating marginal aggregates and soil with foamed asphalt*. Association of Asphalt
11 *Paving Technologists*, 1981.
- 12 17. Bissada, A.F., *Structural Response of Foamed-Asphalt-Sand Mixtures in Hot Environments*.
13 *Transportation Research Record*, Vol. 1115: p. 134-149, 1987.
- 14 18. Sakr, H.A. and P.G. Manke, *Innovations in Oklahoma Foamix Design Procedures*.
15 *Transportation Research Board*, Vol. **1034**: p. 26-34, 1985.
- 16 19. Castedo-Franco, L.H. and L.E. Wood. *Stabilisation with Foamed Asphalt of Aggregate*
17 *Commonly Used in Low Volume Road*. in *Low volume road: 3rd International Conference*,
18 Washington, DC: Transportation Research Board, 1983.
- 19 20. Shackel, B., K. Makhiuchi, and J.R. Derbyshire. *The Response of a Foamed Bitumen*
20 *Stabilised Soil to Repeated Triaxial Loading* in ARRB, 1974.
- 21 21. Maccarrone, S., et al. *Pavement Recycling Using Foamed Bitumen*. in *17th ARRB conference*,
22 Queensland, 1994.
- 23 22. Jenkins, K.J., et al. *Advanced Testing for Cold Recycling Treatment Selection on N7 Near*
24 *Cape Town*. . in *8th Conference on Asphalt Pavements for Southern Africa (CAPSA '04)*, Sun
25 City, South Africa, 2004.
- 26 23. Saleh, M.F., *Effect of Rheology on The Bitumen Foamability and Mechanical Properties of*
27 *Foam Bitumen Stabilised Mixes*. The International Journal of Pavement Engineering 2006.
28 **8**(2).
- 29 24. Wirtgen, *Cold Recycling Technology*. 2010.
- 30 25. Academy, A., *A Guideline for the Design and Construction of Bitumen Emulsion and Foamed*
31 *Bitumen Stabilised Materials*. 2009.
- 32 26. Tebaldi, G., et al., *Synthesis of standards and procedures for specimen preparation and in-*
33 *field evaluation of cold-recycled asphalt mixtures*. Road Materials and Pavement Design,
34 2014. **15**(2): p. 272-299.
- 35 27. West, R., Willis, J.R., and Marasteanu, M., *Improved mix design, evaluation, and materials*
36 *management practices for hot mix asphalt with high reclaimed asphalt pavement content*, in
37 *NCHRP 752*. 2013, National Center for Asphalt Technology: Auburn, AL.
- 38 28. Petrauskas, M., *Use of Cold Mix with RAP in Lithuania*, in *26th International Baltic Road*
39 *Conference*. 2006: Kuressaare.
- 40 29. Long, F.M., H.L. Theyse, and D.F.C. Ventura, *Characterization of Foamed Bitumen Treated*
41 *Materials from HVS Test Sections*. 2004, CSIR Transportek: Pretoria, South Africa.
- 42 30. Flintsch, G.W., R. Dymond, and J. Collura, *Pavement Management Applications Using*
43 *Geographic Information Systems*, in *NCHRP Synthesis report 335*. 2004.
- 44 31. Haas, R. *Reinventing the (Pavement management) Wheel*. in *Fifth International Conference*
45 *On Managing Pavements*. 2001. Seattle, Washington: Distinguished Lecture.
- 46 32. McNerney, M.T. and T. Rioux, *Geographic Information System (GIS) Needs Assesment for*
47 *TXDOT Pavement Management Information Systems*. 2000, THE UNIVERSITY OF TEXAS
48 AT AUSTIN.
- 49 33. Cazacliu, B., et al., *Effect of Process Parameters on Foam Bitumen-based Road Material*
50 *Production at Ambient Temperature*. Road Materials and Pavement Design, 2008. **9**(3): p.
51 499-523.